

Green nanotechnology: a review on green synthesis of silver nanoparticles — an ecofriendly approach

This article was published in the following Dove Press journal:
International Journal of Nanomedicine

Shabir Ahmad¹
Sidra Munir¹
Nadia Zeb^{1,2}
Asad Ullah¹
Behramand Khan¹
Javed Ali³
Muhammad Bilal³
Muhammad Omer⁴
Muhammad Alamzeb⁵
Syed Muhammad Salman¹
Saqib Ali⁵

¹Department of Chemistry, Islamia College University, Peshawar 25120, Pakistan; ²Department of Chemistry, Government Girls Degree College, Peshawar, Pakistan; ³Department of Chemistry, Kohat University of Science and Technology, Kohat, Pakistan; ⁴Institute of Chemical Sciences, University of Swat, Swat, 19201, Pakistan; ⁵Department of Chemistry, University of Kotli 11100, Azad Jammu and Kashmir, Pakistan

Background: Nanotechnology explores a variety of promising approaches in the area of material sciences on a molecular level, and silver nanoparticles (AgNPs) are of leading interest in the present scenario. This review is a comprehensive contribution in the field of green synthesis, characterization, and biological activities of AgNPs using different biological sources.

Methods: Biosynthesis of AgNPs can be accomplished by physical, chemical, and green synthesis; however, synthesis via biological precursors has shown remarkable outcomes. In available reported data, these entities are used as reducing agents where the synthesized NPs are characterized by ultraviolet-visible and Fourier-transform infrared spectra and X-ray diffraction, scanning electron microscopy, and transmission electron microscopy.

Results: Modulation of metals to a nanoscale drastically changes their chemical, physical, and optical properties, and is exploited further via antibacterial, antifungal, anticancer, antioxidant, and cardioprotective activities. Results showed excellent growth inhibition of the microorganism.

Conclusion: Novel outcomes of green synthesis in the field of nanotechnology are appreciable where the synthesis and design of NPs have proven potential outcomes in diverse fields. The study of green synthesis can be extended to conduct the in silico and in vitro research to confirm these findings.

Keywords: green synthesis, plant mediated synthesis, silver bioactivity, microorganism

Introduction

Nanotechnology offers fields with effective applications, ranging from traditional chemical techniques to medicinal and environmental technologies. AgNPs have emerged with leading contributions in diverse applications, such as drug delivery,³¹ ointments, nanomedicine,³⁷ chemical sensing,⁴¹ data storage,⁴⁷ cell biology,⁵⁴ agriculture, cosmetics,⁶⁰ textiles,¹⁷ the food industry, photocatalytic organic dye-degradation activity,⁶⁴ antioxidants,⁶⁶ and antimicrobial agents.⁶⁸

Despite the contradictions reported on the toxicity of AgNPs,⁶⁹ its role as a disinfectant and antimicrobial agent has been given considerable appreciation. The available documented data^{73,74} and the interest of the community in this field prompted us to work on plant-mediated green synthesis and biological activities of AgNPs.

Different types of nanoparticles

Some distinctive reported forms of nanoparticles (NPs) are core-shell NPs,⁷⁶ photochromic polymer NPs,⁷⁸ polymer-coated magnetite NPs,⁸⁰ inorganic NPs, AgNPs,

Correspondence: Shabir Ahmad
Department of Chemistry, Islamia College University, Peshawar 25120, Pakistan
Tel +92 345 307 3759
Email shabir.ahmad@icp.edu.pk

CuNPs,⁸² AuNPs,⁸⁵ PtNPs,⁸⁶ PdNPs,⁸⁸ SiNPs,⁸⁹ and NiNPs,⁹¹ while others are metal oxide and metal dioxide NPs, such as ZnONPs,⁹⁴ CuO NPs,⁹⁵ FeO,⁹⁷ MgONPs,¹⁰⁰ TiO₂ NPs,¹⁰² CeO₂ NPs,¹⁰³ and ZrO₂ NPs.¹⁰⁴ Each of these

has an exclusive set of characteristics and applications, and can be synthesized by either conventional or unconventional methods. An extensive classification of NPs is provided in Figure 1.^{105–111}

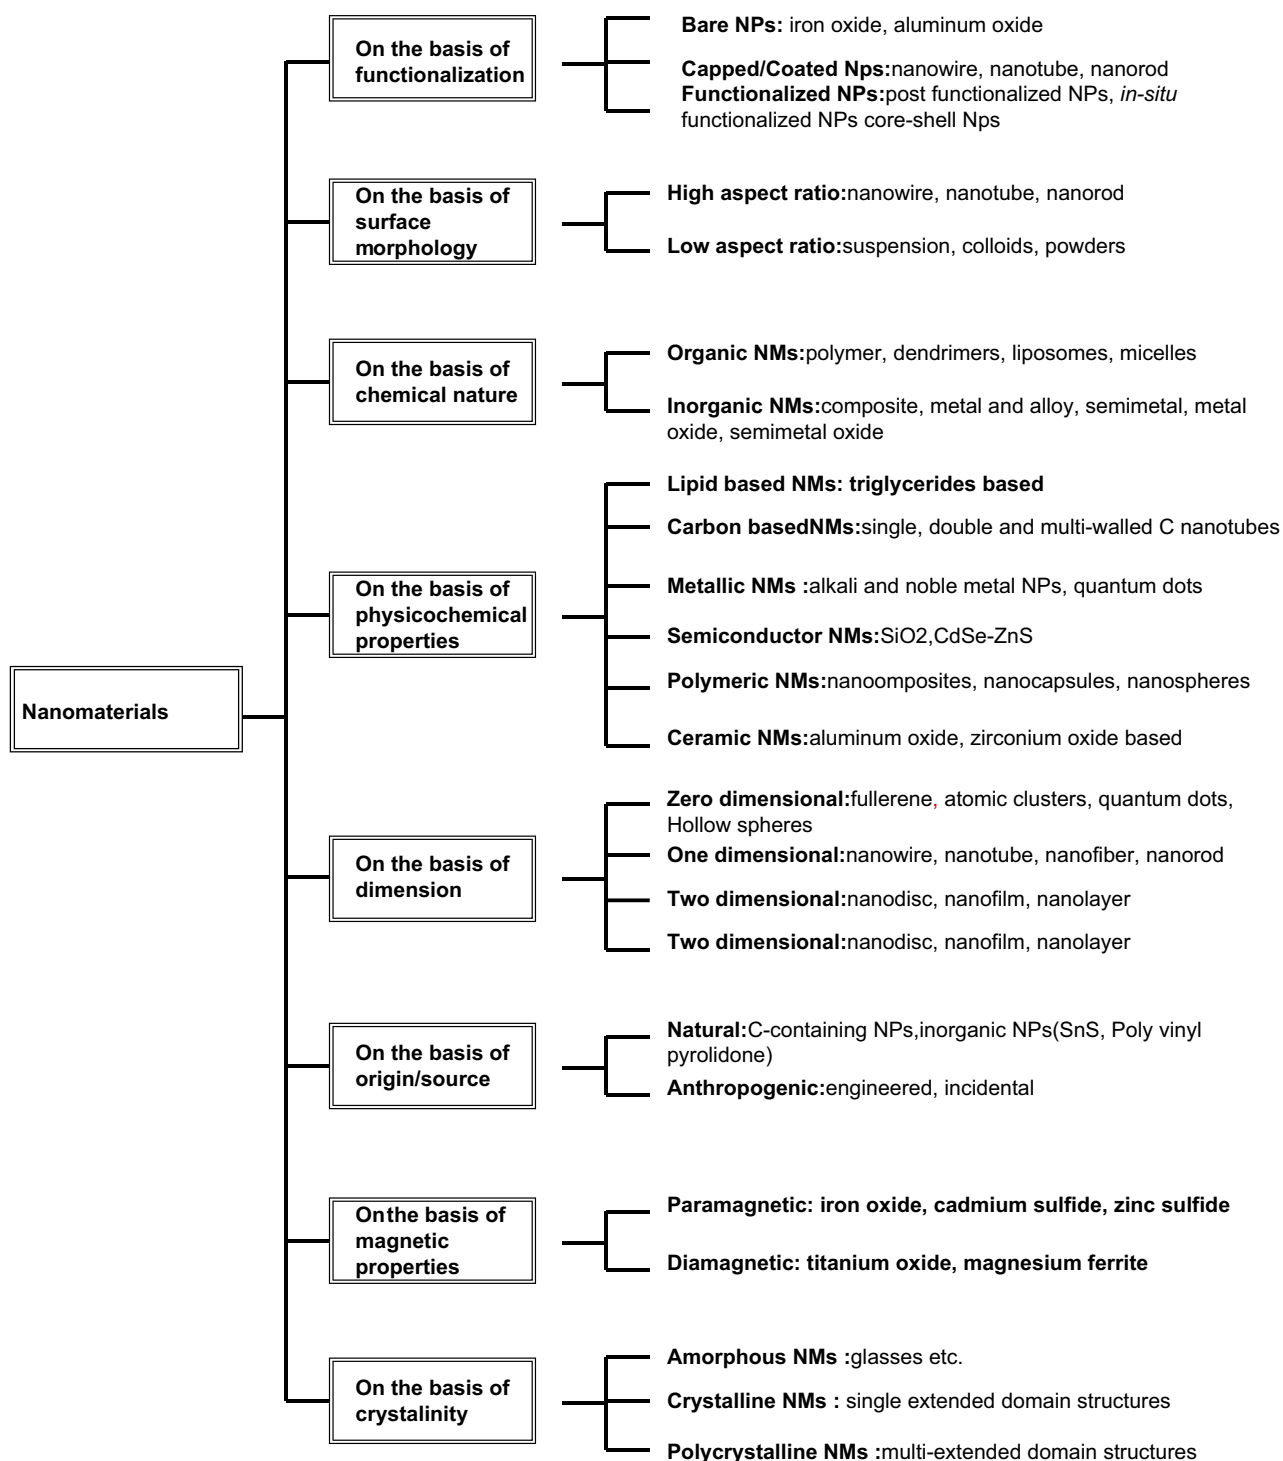


Figure 1 Different approaches to nanomaterial (NM) classification.

Abbreviation: NPs, nanoparticles.

Table 1 Chemical and physical synthesis of AgNPs

Type	Reducing agent	Characterization	Biological activities	Reference
Chitosan-loaded AgNPs	Polysaccharide chitosan	TEM, FTIR, XRD, DSC, TGA	Antibacterial	114
PVP-coated AgNPs	Sodium borohydride	UV-vis, TEM, EDS, DLS, FI-FFF	NANA	115
AgNPs	Ascorbic acid	UV-vis, EFTEM	Antibacterial	116
AgNPs	Hydrazine, D-glucose	UV-vis, TEM	Antibacterial	117
Polydiallyldimethylammonium chloride_ and poly-methacrylic acid-caped AgNPs	Methacrylic acid polymers	UV-vis, reflectance spectrophotometry	Antimicrobial	118

Abbreviations: NPs, nanoparticles; TEM, transmission electron microscopy; FTIR, Fourier-transform infrared; XRD, X-ray diffraction; DSC, differential scanning calorimetry; TGA, thermogravimetric analysis; UV-vis, ultraviolet-visible (spectroscopy); EDS, energy-dispersive spectroscopy; DLS, dynamic light scattering; FI-FFF, flow field-flow fractionation; EFTEM, energy-filtered TEM; NA, not applicable.

Nanoparticle synthesis


Comprehensive approaches available for NP synthesis are bottom-up and top-down.¹¹² The latter approach is immoderate and steady, whereas the former involves self-assembly of atomsize particles to grow nanosize particles. This can be achieved by physical and chemical means,¹¹³ as summarized in Table 1. However, ecofriendly green syntheses are economical, and proliferate and trigger stable NP formation, as shown in Figure 2.

Green approach (biological/ conventional methods)

The surging popularity of green methods has triggered synthesis of AgNPs using different sources, like bacteria, fungi, algae, and plants, resulting in large-scale production with less contamination. Green synthesis is an ecofriendly and biocompatible process,¹¹⁹ generally accomplished by using a capping agent/stabilizer (to control size and prevent agglomeration),¹²⁰ plant extracts, yeast, or bacteria.¹²¹

Green synthesis using plant extracts

In contrast to microorganisms, plants have been exhaustively used, as apparent from Table 2. This is because plant phytochemicals show greater reduction and stabilization.¹²² *Eugenia jambolana* leaf extract was used to synthesize AgNPs that indicated the presence of alkaloids, flavonoids, saponins, and sugar compounds.¹²³ Bark extract of *Saraca asoca* indicated the presence of hydroxylamine and carboxyl groups.¹²⁴ AgNPs using leaves of *Rhynchosyris ellipticum* were synthesized, and the results indicated the presence of polyphenols, flavonoids, alkaloids, terpenoids, carbohydrates, and steroids.¹²⁵ *Hesperidin* was used to form AgNPs

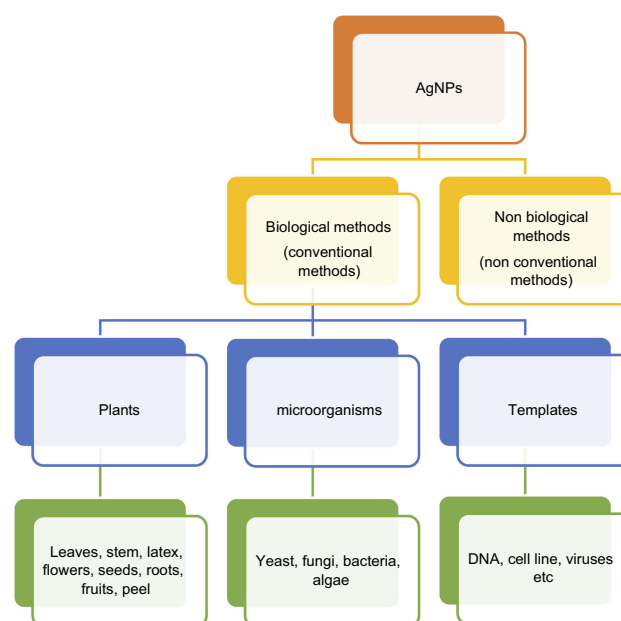**Figure 2** Various approaches to the synthesis of Ag nanoparticles (NPs).

of 20–40 nm.¹²⁶ Phenolic compounds of pyrogallol and oleic acid were reported to be essential for the reduction of silver salt to form NPs.¹²⁷ Pepper-leaf extract acts as a reducing and capping agent in the formation of AgNPs of 5–60 nm.¹²⁸ Fruit extracts of *Malus domestica* acted as a reducing agent. Similarly, *Vitis vinifera*,³⁹ Andean blackberry,¹²⁹ *Adansonia digitata*,¹³⁰ *Solanum nigrum*,¹³¹ *Nitraria schoberi*,¹³² or multiple fruit peels have also been reported for AgNP synthesis.¹³³ Combinations of plant extracts have also been reported.¹³⁴ Some other reductants used for AgNO₃ are polysaccharide,¹³⁵ soluble starch,¹³⁶ natural rubber,¹³⁷ tarmac,¹³⁸ cinnamon,²⁵ stem-derived callus of green apple,²⁵ red apple,¹³⁹ egg white,¹⁴⁰ lemon grass,¹⁴¹ coffee,¹⁴² black

Table 2 Plant-mediated synthesis of AgNPs

Plant (Family)-Local Name	Part	Characterization	Phytoconstituents Present in plant	Size of AgNPs	Shape of AgNPs	Reference
<i>Acacia nilotica</i> (Fabaceae) — babul	Pod	UV-vis, HRTEM, FTIR, DLS, EDS, XRD, ζ -potential	Gallic acid, ellagic acid, epicatechin, rutin	HRTEM (20–30 nm)	Distorted spherical	151
<i>Ocimum sanctum</i> (Lamiaceae) — tulsi	Fresh leaf	UV-vis, TEM, XRD, FTIR	Alkaloids, glycosides, tannins, saponins, aromatic compounds	TEM (3–20 nm, average 9.5 nm)	Spherical	152
<i>Citrullus colocynthis</i> (Cucurbitaceae) — bitter apple	Fresh leaf	UV-vis, FTIR, AFM	NA	AFM (31 nm)	Spherical	153
<i>Coccinia grandis</i> (Cucurbitaceae) — ivy gourd	Fresh leaf	UV-vis, HRTEM, SEM, XRD, FTIR, TGA, EDS	Triterpenoids, alkaloids, tannin	TEM (20–30 nm)	Spherical	154
<i>Pterocarpus santalinus</i> (Fabaceae) — sandalwood	Fresh leaf	UV-vis, SEM, XRD, FTIR, AFM, EDX	NA	SEM (20–50 nm, average 20 nm), AFM (41 nm)	Spherical	155
<i>Coleus aromaticus</i> (Lamiaceae) — borage	Fresh leaf	UV-vis, XRD, FTIR, EDAX	Carvacrol, caryophyllene, patchoulene, flavonoids	SEM (40–50 nm)	Spherical	156
<i>Jatropha curcas</i> (Euphorbiaceae) — physic nut	Seed	UV-vis, HRTEM, XRD	NA	HRTEM (1,550 nm) at 10^{-3} M and 30–50 nm at 10^{-2} M	Spherical (at 10^{-3} M), unevenly shaped (at 10^{-2} M)	157
<i>Melia dubia</i> (Meliaceae) — malai vembu	Fresh leaf	UV-vis, TEM, SEM-EDS, XRD	Alkaloids, carbohydrates, glycosides, phenolic compounds, tannins, gums, mucilages	XRD (average 7.3 nm)	Irregular, but mostly spherical	158
<i>Capsicum annuum</i> (Solanaceae) — peppers	Fresh leaf	UV-vis, TEM, FTIR, SAED, XRD, XPS, CV, DPV	Proteins/enzymes, polysaccharides, amino acids, vitamins	TEM (10±2 nm at 5 hours)	Spherical	159
<i>Annona squamosa</i> (Annonaceae) — sweetsops	Young leaf	UV-vis, XRD, TEM, FTIR, EDS, ζ -potential	Glycoside, alkaloids, saponins, flavonoids, tannins phenolic compounds, phytoosterols	TEM (20–100 nm)	Spherical	160
<i>Camellia sinensis</i> (Theaceae) — tea	Dried leaf	XRD, TEM, FTIR	NA	Debye-Scherrer equation (3.42 nm), TEM (2–10 nm, average 4.06 nm)	Spherical	161

(Continued)

Table 2 (Continued).

Plant (Family)-Local Name	Part	Characterization	Phytoconstituents Present in plant	Size of AgNPs	Shape of AgNPs	Reference
<i>Citrus sinensis</i> (Rutaceae) — orange	Peel extract	UV-vis, TEM, FESEM, FTIR, XRD, EDAX	Vitamin C, flavonoids, acids, volatile oils	XDS (33±3 nm at 25°C, 8±2 nm at 60°C), HRTEM (35±2 nm)	Spherical	38
<i>Lantana camara</i> (Verbenaceae) — wild/red sage	Fresh leaf	UV-vis, TEM, FESEM, FTIR, XRD, XPS, AFM, SAED	Phenolics, flavonoids, terpenoids, alkaloids, lipids, proteins, carbohydrates	FESEM (34 nm), AFM (17–31 nm), TEM (14–27 nm), XRD (11–24 nm), SAED (~14 nm)	Spherical	162
<i>Coriandrum sativum</i> (Apiaceae) — coriander	Fresh leaf	UV-vis, TEM, FTIR, XRD, Z-scan techniques	Carotene, thiamine, riboflavin, niacin, oxalic acid, sodium	TEM (8–75 nm, average 26 nm)	Spherical	163
<i>Aloe vera</i> (Asphodelaceae) — first-aid plant	Fresh leaf	UV-vis, TEM, FTIR, AFM, NIR absorption spectroscopy	NA	TEM (15.2±4.2 nm)	Spherical	164
<i>Memecylon edule</i> (Melastomataceae) — delek bangas	Shade-dried leaf	UV-vis, TEM, SEM, FTIR, EDAX	Triterpenes, tannins, flavonoids, saponin	TEM (50–90 nm)	Square	165
<i>Hibiscus rosa-sinensis</i> (Malvaceae) — rose mallow	Leaf	UV-vis, TEM, FTIR, XRD, SAED	Proteins, vitamin C, organic acids (essentially malic acid), flavonoids, anthocyanins	TEM (average size 13 nm), Scherrer equation (13 nm)	Spherical	166
<i>Cinnamomum camphora</i> (Lauraceae) — camphorwood	Fresh leaf	UV-vis, TEM, SEM, XRD, AFM	NA	TEM (55–80 nm, average diameter 64.8 nm)	Quasispherical	55
<i>Piper longum</i> (Piperaceae) — pipli	Dried fruit powder	UV-vis, SEM, FTIR, DLS	Piperidine, alkaloids, tannins, dihydrotigmasterol, sesamin, terpenes	DLS (15–200 nm, average 46 nm)	Spherical	167
<i>Sesbania grandiflora</i> (Fabaceae) — hummingbird tree	Fresh leaf	UV-vis, FE-TEM, FTIR, XRD, SAED	Carboxylic compounds, flavonoids, terpenoids, polyphenols	TEM (10–50 nm, average 24.1 nm), XRD (18.52 nm)	Spherical	168
<i>Moringa oleifera</i> (Moringaceae) — drumstick tree	Fresh stem bark	UV-vis, TEM, HRSEM, FTIR, DLS, AFM	Phenols, β-sitosterol, caffeoylquinic acid, quercetin, kaempferol	HRTEM (average size 40 nm), DLS (38 nm), SEM (40 nm)	Spherical and pentagonal	169
<i>Origanum vulgare</i> (Lamiaceae) — oregano	Leaves	UV-vis, FESEM, FTIR, XRD, DLS, ζ-potential	NA	FESEM (63–85 nm), Scherrer formula (65 nm), DLS (136±10.09 nm)	Spherical	170

(Continued)

Table 2 (Continued).

Plant (Family)-Local Name	Part	Characterization	Phytoconstituents Present in plant	Size of AgNPs	Shape of AgNPs	Reference
<i>Vitex negundo</i> (Lamiaceae) — Chinese chaste tree	Fresh leaf	UV-vis, TEM, FESEM, FTIR, XRD, EDX	Alkaloids, glycosides, flavonoids, phenolic compounds, reducing sugars, resin tannins	TEM (5–47 nm)	Spherical	171
<i>Tephrosia tinctoria</i> (Fabaceae) — alu pila	Shade dried stem extract	UV-vis, TEM, SEM, FTIR	Phenol, flavonoids	TEM (73 nm)	Spherical	172
<i>Minusops elengi</i> (Sapotaceae) — Spanish cherry	Seed	UV-vis, TEM, FTIR, XRD, HPLC	Ascorbic acid, gallic acid, pyrogallol, resorcinol	TEM (12.8–30.48 nm)	Spherical	173
<i>Alternanthera dentata</i> (Amaranthaceae) — Joseph's coat	Leaf	FTIR, TEM, SEM, XRD	NA	SEM (50–100 nm)	Spherical	174
<i>Sesuvium portulacastrum</i> (Aizoaceae) — salt marsh	Leaf	UV-vis, TEM, FTIR, XRD	NA	TEM (5–20 nm)	Spherical	175
<i>Dalbergia spinosa</i> (Fabaceae) — liana	Shade-dried leaf	UV-vis, TEM, FTIR, DLS	Flavonoids, isoflavonoids, neoflavonoids, steroids, terpenoids	TEM (18±4 nm)	Spherical	176
<i>Sambucus nigra</i> (Adoxaceae) — European black elderberry	Frozen fruit	UV-vis, FTIR, XRD, ζ-potential	Polyphenol anthocyanins	TEM (20–80 nm)	Spherical	177
<i>Millingtonia hortensis</i> (Bignoniaceae) — neem	Dried leaf	NA	NA	2–8 nm	NA	178
<i>Syzygium cumini</i> (Myrtaceae) — jamun	Air-dried seed	UV-vis, SEM, XRD, FTIR, DLS, ζ-potential, HPLC	Gallic acid, p-coumaric acid, quercetin, 3,4-dihydroxybenzoic acid	SEM (40–100 nm), average 43.02 nm, Z-average 43±1.25	Irregular spherical contour	179
<i>Mukia maderaspatana</i> (Cucurbitaceae) — Madras pea pumpkin	Fresh leaf	UV-vis, FESEM, FTIR, XRD, ART	NA	FESEM (13–34 nm), Debye-Scherrer formula (64 nm)	Spherical	180
<i>Nelumbo nucifera</i> (Nelumbonaceae) — sacred lotus	Fresh leaf	UV-vis, TEM, SEM, FTIR, XRD	Betulinic acid, steroidal pentacyclic triterpenoid, procyanidins	TEM (25–80 nm, average 45 nm), SEM (25–80 nm)	Spherical (TEM), triangular (SEM)	181

(Continued)

Table 2 (Continued).

Plant (Family)-Local Name	Part	Characterization	Phytoconstituents Present in plant	Size of AgNPs	Shape of AgNPs	Reference
<i>Rhizophora mucronata</i> (Rhizophoraceae) — mangrove	Leaf	UV-vis, FTIR, XRD, AFM	Alkaloids, flavonoids, polyphenols, terpenoids	AFM (60–95 nm)	Spherical	182

Abbreviations: CV, Cyclic voltammograms; ART, total reflectance technique; NPs, nanoparticles; UV-vis, ultraviolet-visible spectroscopy; TEM, transmission electron microscopy; SEM, scanning electron microscopy; FESEM, field-emission SEM; HREM, high-resolution transmission electron microscopy; XRD, X-ray diffraction; FTIR, Fourier-transform infrared spectroscopy; AFM, atomic force microscopy; HPLC, high-performance liquid chromatography; DLS, dynamic light scattering; EDX, energy-dispersive X-ray (spectroscopy); EDAX, ED X-ray analysis; SAED, selected-area electron diffraction; TGA, thermogravimetric analysis; NA, not available; CV; ART, .

tea,¹⁴³ and *Abelmoschus esculentus* juice.¹⁴⁴ Besides these, an extensive diagram representing different parts of different plant leaves, eg, peel, seed, fruit, bark, flower, stem, and root, also used in nanoformulations, is given in Figure 3. Green synthesis is economical and innocuous.^{30,38,150}

Biosynthesis using microorganisms

Bacteria-mediated synthesis of AgNPs

Microorganisms like fungi, bacteria, and yeast are of huge interest for NP synthesis; however, the process is threatened by culture contamination, lengthy procedures, and less control over NP size. NPs formed by microorganisms can be classified into distinct categories, depending upon the location where they are synthesized.¹⁸³ Otari et al synthesized AgNPs intracellularly using Actinobacteria *Rhodococcus* sp. NCIM 2891.¹⁸⁴ Kannan et al biosynthesized AgNPs using *Bacillus subtilis* extracellularly.¹⁸⁵ Table 3 provides some illustrative examples of the synthesis of AgNPs using different bacterial strains.

Alga-mediated synthesis of AgNPs

A diverse group of aquatic microorganisms, algae have been used substantially and reported to synthesize AgNPs. They vary in size, from microscopic (picoplankton) to macroscopic (Rhodophyta). AgNPs were synthesized using microalgae *Chaetoceros calcitrans*, *C. salina*, *Isochrysis galbana*, and *Tetraselmis gracilis*.¹⁹⁹ *Cystophora moniliformis* marine algae were used by Prasad et al as a reducing and stabilizing agent to synthesize AgNPs.²⁰⁰ Table 4 illustrates some examples of the micro and macro-algae used for AgNPs synthesis.

Fungus-mediated synthesis of AgNPs

Extracellular synthesis of AgNPs using fungi is also a viable alternative, because of their economical large-scale production. Fungal strains are chosen over bacterial species, because of their better tolerance and metal-bioaccumulation property. Table 5 gives some of the fungal strains used for AgNP synthesis.

Synthesis from miscellaneous sources

Nanotechnology has placed DNA on a recent drive to be used as a reducing agent.²¹⁵ Strong affinity of DNA bases for silver make it a template stabilizer.²¹⁶ AgNPs were synthesized on DNA strands and found to be possibly located at N⁷ guanine and phosphate.²¹⁷ Another attempt



Figure 3 Plant mediated synthesis of AgNPs.

Table 3 Bacteria-mediated synthesis of AgNPs

Reducing agent: bacterial strain	Characterization	Size	Shape	Gram ⁺ / Gram ⁻	Reference
<i>Serratia nematodiphila</i>	UV-vis, SEM, EDS	SEM (65–70 nm)	Spherical	Gram ⁺	186
<i>Bacillus stearothermophilus</i>	UV-vis, TEM, FTIR, DLS	TEM (9.96–22.7 nm, average 14±4 nm)	Spherical	Gram ⁺	187
<i>Bacillus</i> strain CSI I	UV-vis, TEM	TEM (42–92 nm)	NA	Gram ⁺	188
Exopolysaccharide-producing strain <i>Leuconostoc lactis</i>	UV-vis, TEM, SEM, AFM, XRD, TGA-DTA, Raman spectroscopy	TEM (30–200 nm, average 35 nm), AFM (average 30 nm)	Spherical	Gram ⁺	189
<i>Escherichia coli</i>	NA	NA	NA	Gram ⁻	190
<i>Streptomyces hygroscopicus</i>	UV-vis, TEM, EDXA, FE XRD, BioAFM	TEM (20–30 nm)	More or less spherical	Gram ⁺	191
<i>Pediococcus pentosaceus</i> , <i>Enterococcus faecium</i> , <i>Lactococcus garvieae</i>	NA	NA	NA	NA	192
<i>Bacillus cereus</i> , <i>B. subtilis</i> , <i>Escherichia coli</i> , <i>Enterobacter cloacae</i> , <i>Klebsiella pneumoniae</i> , <i>Lactobacillus acidophilus</i> , <i>Staphylococcus aureus</i> , <i>Pseudomonas aeruginosa</i>	UV, TEM, EDS	TEM (28.2–122 nm, average 52.5 nm)	NA	Gram ⁺ and Gram ⁻	193
<i>Morganella morganii</i> RP42	UV, TEM, XRD, SAED	TEM (10–50 nm)	Quasispherical	Gram ⁻	194
<i>Escherichia coli</i>	UV, FTIR, XRD	TEM (average 50 nm)	Spherical	Gram ⁻	195
<i>Pseudomonas antarctica</i> , <i>P. proteolytica</i> , <i>P. meridiana</i> , <i>Arthrobacter kerguelensis</i> , <i>A. gangotriensis</i> , <i>Bacillus indicus</i> , <i>B. cecembensis</i>	UV, TEM, AFM	TEM (6.1±2.8 nm), AFM (4.6–13.3 nm)	Spherical	Gram ⁺ and Gram ⁻	196
<i>Staphylococcus aureus</i>	UV, AFM	AFM (160–180 nm)	Irregular	Gram ⁻	197
<i>Bacillus brevis</i> (NCIM 2533)	UV-vis, SEM, FTIR, AFM, TLC	SEM (22–60 nm, average 41 nm), AFM (average 68 nm)	Spherical	Gram ⁺	198

Abbreviations: NPs, nanoparticles; UV-vis, ultraviolet-visible (spectroscopy); TEM, transmission electron microscopy; SEM, scanning electron microscopy; FESEM, field-emission SEM; HRSEM, high-resolution TEM; XRD, X-ray diffraction; FTIR, Fourier-transform infrared (spectroscopy); AFM, atomic force microscopy; HPLC, high-performance liquid chromatography; DLS, dynamic light scattering; EDX, energy-dispersive X-ray (spectroscopy); EDAX, ED X-ray analysis; SAED, selected-area electron diffraction; TGA, thermogravimetric analysis; NA, not available; TLC, thin-layer chromatography.

Table 4 Alga-mediated synthesis of AgNPs

Reducing agent: alga strain	Characterization	Size	Shape	Algae type	Macro/microalgae	Reference
<i>Sargassum wightii</i> Greville	UV, TEM, XRD, FTIR	TEM (8–27 nm)	Spherical	Brown	Macroalgae	201
<i>Caulerpa racemosa</i>	UV, TEM, FTIR, XRD	TEM (10 nm)	Spherical	Green	Macroalgae	202
Polysaccharide extracted from algae: <i>Pterocladia capillacea</i> , <i>Jania rubens</i> , <i>Ulva fasciata</i> , <i>Colpomenia sinusa</i>	UV, TEM, FTIR	TEM (7, 7, 12, and 20 nm for <i>U. fasciata</i> , <i>P. capillacea</i> , <i>J. rubens</i> , and <i>C. sinusa</i> , respectively)	Spherical and triangular	Red and green	Macroalgae	203
<i>Chaetomorpha linum</i>	UV-vis, SEM, FTIR	SEM (3–44 nm, average ~30 nm)	Varied	Green	Macroalgae	204
<i>Chaetoceros calcitran</i> , <i>Chlorella salina</i> , <i>Isochrysis galbana</i> , <i>Tetraselmis gracilis</i>	UV, SEM	SEM (53.1–73.9 nm)	NA	Green	Microalgae	199
<i>Gelidium amansii</i>	UV-vis, SEM, FTIR	SEM (27–54 nm)	Spherical	Red	Macroalgae	205

Abbreviations: NPs, nanoparticles; UV-vis, ultraviolet-visible (spectroscopy); TEM, transmission electron microscopy; SEM, scanning electron microscopy; XRD, X-ray diffraction; FTIR, Fourier-transform infrared (spectroscopy).

Table 5 Fungus-mediated synthesis of AgNPs

Fungal species used	Characterization	Size	Shape	Reference
<i>Fusarium oxysporum</i>	UV-vis, TEM, FTIR	TEM (5–50 nm)	Spherical and few triangular	206
<i>Verticillium</i>	UV-vis, TEM, SEM, EDX	TEM (25–12 nm)	Spherical	207
<i>Aspergillus fumigatus</i>	UV-vis, TEM, XRD	TEM (5–25 nm)	Spherical and triangular	208
<i>Penicillium fellutanum</i>	UV-vis, TEM	TEM (5–25 nm)	Spherical	209
<i>Aspergillus flavus</i>	UV-vis, TEM, FTIR, XRD	TEM (8.92±1.61 nm)	NA	210
<i>Fusarium semitectum</i>	UV-vis, TEM, FTIR, XRD	TEM (10–60 nm)	Spherical	211
<i>Alternaria alternata</i>	UV-vis, TEM, SEM, FTIR, EDX	SEM (20–60 nm, average 32.5 nm)	Spherical	212
<i>Rhizopus stolonifer</i>	UV-vis, TEM, SEM, FTIR, AFM	TEM (3 and 20 nm)	Spherical	213
<i>Phanerochaete chrysosporium</i>	UV-vis, TEM, FTIR, AFM, TLC	TEM (34–90 nm)	Spherical and oval	214

Abbreviations: NPs, nanoparticles; UV-vis, ultraviolet-visible (spectroscopy); TEM, transmission electron microscopy; SEM, scanning electron microscopy; EDX, energy-dispersive X-ray (spectroscopy); XRD, X-ray diffraction; FTIR, Fourier-transform infrared (spectroscopy); AFM, atomic force microscopy; TLC, thin-layer chromatography.

was made with calf-thymus DNA to synthesize AgNPs.²¹⁸ Similarly, silver-binding peptides were identified and selected using a combinatorial approach for NP synthesis.²¹⁹

Bioactivities

Antibacterial activity of AgNPs

As a broad-spectrum antibiotic, silver is highly toxic to bacteria. It has been of great interest for the past couple of years, due to its wide spectrum of pharmacological activities, with applications in the fields of agriculture, textiles, and especially medicine. Some attributed contributions are given in [Table 6](#).

Antifungal activity of AgNPs

Resistant pathogenic activities of bacteria and fungi have increased invasive infections at an alarming rate.

Ultimately, the subsequent need is to find more potent antifungal agents. [Table 7](#) provides some examples from the literature that have reported antifungal properties of green synthesized AgNPs.

Anticancer activity of AgNPs

The paramount need of today is the synthesis of effective anticancer treatment, as cardiovascular at the top most; cancer is the second most leading cause of human dysphoria. Therefore the synthesis of anticancer agents is of the utmost necessity. AgNPs also possess substantial anticancer activities,²³⁹ as shown in [Table 8](#).

Anti-inflammatory activity of AgNPs

AgNPs of 20–80 nm were synthesized using *Sambucus nigra* (blackberry) extract. The NPs were characterized using ultraviolet-visible and Fourier-transform infrared

Table 6 Antibacterial activities of AgNPs

Biological entity	Testmicroorganism	Method	Reference
<i>Citrullus colocynthis</i>	<i>Escherichia coli</i>	Agar diffusion method	153
<i>Perocarpus santalinus</i>	<i>E. coli</i>	NA	154
<i>Madhuca longifolia</i> flower extract	<i>Bacillus cereus</i> , <i>Staphylococcus saprophyticus</i> , <i>E. coli</i> , <i>Salmonella typhimurium</i>	Agar well diffusion method	220
<i>Aspergillus clavatus</i> fungus	<i>E. coli</i> , <i>Pseudomonas aeruginosa</i>	NA	221
<i>Chenopodium murale</i> leaf extract	<i>E. coli</i>	Cup-plate agar-diffusion method	222
<i>Iresine herbstii</i> leaf extract	<i>Staphylococcus aureus</i> , <i>Enterococcus faecalis</i> , <i>E. coli</i>	Agar-diffusion method	223
Beetroot	<i>E. coli</i> , <i>P. aeruginosa</i> , <i>Staphylococcus</i> , <i>Streptococcus</i>	NA	224
<i>Dioscorea bulbifera</i> plant	<i>St. aureus</i> , <i>E. faecalis</i> , <i>E. coli</i>	Disk diffusion method	225
<i>Rosa indica</i> flower petals	<i>E. coli</i> , <i>P. aeruginosa</i> , <i>Staphylococcus</i> , <i>Streptococcus</i>	Agar well diffusion method	226
<i>Ocimum tenuiflorum</i> plant	NA	Agar well diffusion method	227
<i>Cassia fistula</i> fruit extract	<i>E. coli</i> , <i>Klebsiella pneumonia</i>	Disk diffusion method	114
Chitosan polymer	<i>S. aureus</i>	Parallel-streak method, colony-counting method	228
Chitosan polymer	<i>E. coli</i> (ATCC 25922), <i>S. aureus</i> (ATCC 6538)	Agar disk diffusion method	229
Oxidized AgNPs	<i>E. coli</i>	Cup-plate agar-diffusion method	230
Gallic acid	<i>E. coli</i>	Microdilution method	73
AgNPs	<i>E. coli</i> , <i>Vibrio cholerae</i> , <i>P. aeruginosa</i> , <i>Salmonella typhi</i>	Agar diffusion method	

Abbreviations: NPs, nanoparticles; NA, not available.

Table 7 Antifungal properties of AgNPs

Biological entity used for reduction	Fungal species used as test organism	Characterization	Reference
Green and black tea leaves	<i>Aspergillus flavus</i> , <i>A. parasiticus</i>	UV-vis, SEM, FTIR, EDX	231
Waste dried grass	<i>Fusarium solani</i> , <i>Rhizoctonia solani</i>	UV-vis, TEM, XRD	232
<i>Dodonaea viscosa</i> and <i>Hyptis suaveolens</i> leaf extracts	<i>Candida albicans</i> (ATCC 90028), <i>C. glabrata</i> (MTCC 184), clinical isolate (MTCC 11,802)	FTIR, SEM, XRD, DLS, ζ -potential	233
Cysteine and maltose	<i>C. albicans</i> (ATCC 10231), <i>C. parapsilosis</i> (ATCC 22019)	UV-vis, TEM, SEM, DLS	234
Lignin	<i>A. niger</i>	UV-vis, TEM, SEM, EDS, XRD	235
Cyanobacterium <i>Nostoc</i> strain HKAR2 cell extract	<i>A. niger</i> , <i>Trichoderma harzianum</i>	UV-vis, TEM, SAED, SEM, FTIR, XRD, ζ -potential	236
<i>Bergenia ciliata</i> plant extract	<i>A. fumigatus</i> (FCBP 66), <i>F. solani</i> (FCBP 0291), <i>A. niger</i> (FCBP 0198), <i>A. flavus</i> (FCBP 0064)	UV-vis, SEM, FTIR	237
<i>Trifolium resupinatum</i> seed extract	<i>Neofusicoccum parvum</i> , <i>R. solani</i>	UV-vis, TEM FTIR, XRD	238

Abbreviations: NPs, nanoparticles; UV-vis, ultraviolet-visible (spectroscopy); TEM, transmission electron microscopy; SEM, scanning electron microscopy; XRD, X-ray diffraction; FTIR, Fourier-transform infrared (spectroscopy); DLS, dynamic light scattering; EDX, energy-dispersive X-ray (spectroscopy); EDAX, ED X-ray analysis; SAED, selected-area electron diffraction.

Table 8 Anticancer property of AgNPs

Biological entity used for reduction	Cancer cells under study	Characterization	Reference
<i>Cleome viscosa</i> fruit extract	Lung (A549) and ovarian (PA1) cancer cell lines	UV-vis, TEM, SEM, FESEM, EDAX, FTIR, XRD	240
<i>Annona muricata</i> leaf extract	Human fibroblasts isolated from dermis	UV-vis, TEM, XRD, DLS, ζ -potential	239
N,N,N-trimethyl chitosan chloride and poly-electrolyte complex	Colon cancer cell lines (HCT116) and Mammalian cell lines (African green monkey kidney cell lines (VERO cells)	HRTEM, FESEM, FTIR, EDX, XRD, ^1H NMR	241
<i>Rheum Rhabarbarum</i> fresh stem extract	Cervical carcinoma HeLa cell line	UV-vis, SEM, TEM, FTIR, EDX, TGA, XRD, ζ -potential	242
<i>Matricaria chamomilla</i>	A549 lung cancer cells	UV-vis, TEM, FESEM, FTIR, XRD EDS, DLS	243
<i>Zataria multiflora</i> leaf extract	Cervical carcinoma cells (HeLa cell line)	UV-vis, TEM, FTIR, EDS, DLS, ζ -potential	96
<i>Phoenix dactylifera</i> hair-root extract	Human breast cancer (MCF7 cell line)	UV-vis, TEM, FTIR, XRD, FESEM, EDAX, Nanophox spectra analysis, PCCS	244

Abbreviations: NPs, nanoparticles; UV-vis, ultraviolet-visible (spectroscopy); TEM, transmission electron microscopy; SEM, scanning electron microscopy; FESEM, field-emission SEM; HRTEM, high-resolution TEM; XRD, X-ray diffraction; FTIR, Fourier-transform infrared (spectroscopy); AFM, atomic force microscopy; HPLC, high-performance liquid chromatography; DLS, dynamic light scattering; EDX, energy-dispersive X-ray (spectroscopy); EDAX, ED X-ray analysis; TGA, thermogravimetric analysis; PCCS, .

spectroscopy and X-ray diffraction, and further investigations were carried out for anti-inflammatory effects, both in vitro and in vivo, against Wister rats.¹⁷⁷

Antiviral activity of AgNPs

Multidimensional biological activities of AgNPs provide significant antiviral potentiality. HEPES buffer was used to synthesize NPs of 5–20 nm. Postinfection antiviral activity of AgNPs was evaluated using Hut/CCR5 cells using ELISA. AgNPs inhibited HIV1 retrovirus 17%–187% more than the reverse-transcriptase inhibitor azidothymidine triphosphate.²⁴⁵ Polysulfone-incorporated AgNPs manifested antiviral and antibacterial activity. This was attributed to the release of sufficient silver ions from the membrane, acting as an antiviral agent.²⁴⁶

Cardioprotection

The medicinal herb neem (*Millingtonia hortensis*) has been used to synthesize AgNPs, and showed significant cardioprotective properties in rats.¹⁷⁸

Wound dressing

Nanotechnology has contributed significantly in the area of wound healing, as healing is attributed to increased anti-inflammatory and antimicrobial activity. A cotton fabric treated with NPs of size 22 nm exhibited potent healing power.²⁴⁷ Another advance in this area was made with the impregnation of AgNPs into bacterial cellulose for antimicrobial wound dressing. *Acetobacter xylinum* (strain TISTR 975) was used to produce bacterial cellulose, which was immersed in silver nitrate solution. It was effective against both Gram-positive and Gram-negative bacteria.²⁴⁸ The performance of a polymer is increased by the introduction of inorganic NPs. In this regard, polyurethane solution containing silver ions was reduced by dimethylformamide using electrospinning. Collagen was introduced to increase its hydrophilicity. This collagen sponge incorporating AgNPs had enhanced wound-healing ability in an animal model.²⁴⁹ Most recently, Jacob et al biosynthesized nanoengineered tissue impregnated with AgNPs, which significantly prevented bacterial growth on the surface of tissue and could help in controlling health-associated infections.²⁵⁰

Conclusion

Nature has its own coaching manners of synthesizing miniaturized functional materials. Increasing awareness

of green chemistry and the benefit of synthesis of AgNPs using plant extracts can be ascribed to the fact that it is ecofriendly, low in cost, and provides maximum protection to human health. Green synthesized AgNPs have unmatched significance in the field of nanotechnology. AgNPs cover a wide spectrum of significant pharmacological activities, and the cost-effectiveness provides an alternative to local drugs. Besides plant-mediated green synthesis, special emphasis has also been placed on the diverse bioassays exhibited by AgNPs. This review will help researchers to develop novel AgNP-based drugs using green technology.

Author contributions

All authors contributed to data analysis, drafting or revising the article, gave final approval of the version to be published, and agree to be accountable for all aspects of the work.

Disclosure

The authors report no conflicts of interest in this work.

References

1. Prasad R, Swamy VS. Antibacterial activity of silver nanoparticles synthesized by bark extract of *Syzygium cumini*. *J Nanopart*. 2013;2013:6. doi:10.1155/2013/431218
2. Isaac R, Sakthivel G, Murthy C. Green synthesis of gold and silver nanoparticles using Averrhoa bilimbi fruit extract. *J Nanotechnol*. 2013;2013:6. doi:10.1155/2013/906592
3. Jagtap UB, Bapat VA. Green synthesis of silver nanoparticles using Artocarpus heterophyllus Lam. seed extract and its antibacterial activity. *Ind Crops Prod*. 2013;46:132–137.
4. Phanjom P, Borthakur M, Das R, Dey S, Bhuyan T. Green synthesis of silver nanoparticles using leaf extract of *Amaranthus viridis*. *Int J Nanotechnol Appl*. 2012;6:53–59.
5. Ghoreishi SM, Behpour M, Khayat Kashani M. Green synthesis of silver and gold nanoparticles using Rosa damascena and its primary application in electrochemistry. *Phys E*. 2011;44(1):97–104.
6. Suresh G, Gunasekar PH, Kokila D, et al. Green synthesis of silver nanoparticles using Delphinium denudatum root extract exhibits antibacterial and mosquito larvicidal activities. *Spectrochim Acta A*. 2014;127:61–66.
7. Santhoshkumar T, Rahuman AA, Bagavan A, et al. Evaluation of stem aqueous extract and synthesized silver nanoparticles using Cissus quadrangularis against Hippobosca maculata and Rhipicephalus (Boophilus) microplus. *Exp Parasitol*. 2012;132(2):156–165.
8. Heydari R, Rashidipour M. Green synthesis of silver nanoparticles using extract of oak fruit hull (Jaft): synthesis and in vitro cytotoxic effect on MCF-7 cells. *Int J Breast Cancer*. 2015;2015:6.
9. Rajeshkumar S. Synthesis of silver nanoparticles using fresh bark of Pongamia pinnata and characterization of its antibacterial activity against gram positive and gram negative pathogens. *Resour-Effic Technol*. 2016;2(1):30–35. doi:10.1016/j.reffit.2016.06.003
10. Song JY, Kim BS. Biological synthesis of bimetallic Au/Ag nanoparticles using Persimmon (Diopyros kaki) leaf extract. *Korean J Chem Eng*. 2008;25(4):808–811. doi:10.1007/s11814-008-0133-z

11. Dhand V, Soumya L, Bharadwaj S, Chakra S, Bhatt D, Sreedhar B. Green synthesis of silver nanoparticles using *Coffea arabica* seed extract and its antibacterial activity. *Mater Sci Eng C*. 2016;58:36–43. doi:10.1016/j.msec.2015.08.018
12. Sharma K, Kaushik S, Jyoti A. Green synthesis of silver nanoparticles by using waste vegetable peel and its antibacterial activities. *J Pharm Sci Res*. 2016;8(5):313.
13. Moteriy P, Chanda S. Synthesis and characterization of silver nanoparticles using *Caesalpinia pulcherrima* flower extract and assessment of their in vitro antimicrobial, antioxidant, cytotoxic, and genotoxic activities. *Artif Cells Nanomed Biotechnol*. 2017;45(8):1556–1567. doi:10.1080/21691401.2016.1261871
14. Rao NH, Lakshmi N, Pammi S, Kollu P, Ganapathy S, Lakshmi P. Green synthesis of silver nanoparticles using methanolic root extracts of *Diospyros paniculata* and their antimicrobial activities. *Mater Sci Eng C*. 2016;62:553–557. doi:10.1016/j.msec.2016.01.072
15. Saddal SK, Telang T, Bhange VP, Kopulwar A, Santra S, Soni M. Green synthesis of silver nanoparticles using stem extract of *Berberis aristata* and to study its characterization and antimicrobial activity. *J Pharm Res*. 2018;12(6):840.
16. Dubey SP, Lahtinen M, Sillanpää M. Tansy fruit mediated greener synthesis of silver and gold nanoparticles. *Process Biochem*. 2010;45(7):1065–1071. doi:10.1016/j.procbio.2010.03.024
17. Bharathi D, Josebin MD, Vasantharaj S, Bhuvaneshwari V. Biosynthesis of silver nanoparticles using stem bark extracts of *Diospyros montana* and their antioxidant and antibacterial activities. *J Nanostruct Chem*. 2018;8(1):83–92. doi:10.1007/s40097-018-0256-7
18. Baghizadeh A, Ranjbar S, Gupta VK, et al. Green synthesis of silver nanoparticles using seed extract of *Calendula officinalis* in liquid phase. *J Mol Liq*. 2015;207:159–163. doi:10.1016/j.molliq.2015.03.029
19. Rivera-Rangel RD, González-Muñoz MP, Avila-Rodriguez M, Razo-Lazcano TA, Solans C. Green synthesis of silver nanoparticles in oil-in-water microemulsion and nano-emulsion using geranium leaf aqueous extract as a reducing agent. *Colloids Surf A*. 2018;536:60–67. doi:10.1016/j.colsurfa.2017.07.051
20. Dar P, Waqas U, Hina A, et al. DBiogenic synthesis, characterization of silver nanoparticles using multani mitti (Fullers Earth), tomato (*Solanum lycopersicum*) seeds, rice husk (*Oryza sativa*) and evaluation of their potential antimicrobial activity. *J Chem Soc Pak*. 2016;38(4):665–674.
21. Aboutorabi SN, Nasiriboroumand M, Mohammadi P, Sheibani H, Barani H. Biosynthesis of silver nanoparticles using safflower flower: structural characterization, and its antibacterial activity on applied wool fabric. *J Inorg Organomet Polym Mater*. 2018;28(6):2525–2532. doi:10.1007/s10904-018-0925-5
22. Karthiga P. Preparation of silver nanoparticles by *Garcinia mangostana* stem extract and investigation of the antimicrobial properties. *Biotechnol Res Innovation*. 2018;2(1):30–36. doi:10.1016/j.biori.2017.11.001
23. Baskaran C, Ratha Bai V. Green synthesis of silver nanoparticles using *Coleus forskohlii* roots extract and its antimicrobial activity against *Bacteria* and *Fungus*. *Int J Drug Dev Res*. 2013;5(1):1–10.
24. Swamy MK, Akhtar MS, Mohanty SK, Sinniah UR. Synthesis and characterization of silver nanoparticles using fruit extract of *Momordica cymbalaria* and assessment of their in vitro antimicrobial, antioxidant and cytotoxicity activities. *Spectrochim Acta A*. 2015;151:939–944.
25. Saliem AH, Ibrahim OM, Salih SI. Biosynthesis of silver nanoparticles using cinnamon *zeylanicum* plants bark extract. *مجلة الكوفة للعلوم الطبية البيطرية Kufa J Vet Med Sci*. 2016;7(1):51–63.
26. Nazeruddin G, Prasad N, Prasad S, Shaikh Y, Waghmare S, Adhyapak P. *Coriandrum sativum* seed extract assisted in situ green synthesis of silver nanoparticle and its anti-microbial activity. *Ind Crops Prod*. 2014;60:212–216.
27. Selvakumar P, Sithara R, Viveka K, Sivashanmugam P. Green synthesis of silver nanoparticles using leaf extract of *Acalypha hispida* and its application in blood compatibility. *J Photochem Photobiol B*. 2018;182:52–61.
28. Bharathi D, Kalaichelvan P, Atmaram V, Anbu S. Biogenic synthesis of silver nanoparticles from aqueous flower extract of *Bougainvillea spectabilis* and their antibacterial activity. *J Med Plants*. 2016;4:248–252.
29. Sreelakshmy V, Deepa M, Mridula P. Green synthesis of silver nanoparticles from *glycyrrhiza glabra* root extract for the treatment of gastric ulcer. *J Dev Drugs*. 2016;5(2):152.
30. Tamileswari R, Haniff Nisha M, Jesurani S, et al. Synthesis of silver nanoparticles using the vegetable extract of *raphanus sativus* (Radish) and assessment of their antibacterial activity. *Int J Adv Technol Eng Sci*. 2015;3(5):207–212.
31. Basu S, Samanta HS, Ganguly J. Green synthesis and swelling behavior of Ag-nanocomposite semi-IPN hydrogels and their drug delivery using *Dolichos biflorus* Linn. *Soft Mater*. 2018;16(1):7–19.
32. Iravani S, Zolfaghari B. Green synthesis of silver nanoparticles using *Pinus eldarica* bark extract. *Biomed Res Int*. 2013;2013:5.
33. Gavade SM, Nikam G, Dhabbe R, Sabale S, Tamhankar B, Mulik G. Green synthesis of silver nanoparticles by using *carambola* fruit extract and their antibacterial activity. *Adv Nat Sci*. 2015;6(4):045015.
34. Mittal AK, Kaler A, Banerjee UC. Free Radical Scavenging and Antioxidant Activity of Silver Nanoparticles Synthesized from Flower Extract of *Rhododendron dauricum*. *Nano Biomed Eng*. 2012;4(3):118–124.
35. Upadhyay P, Mishra SK, Purohit S, Dubey G, Singh Chauhan B, Srikrishna S. Antioxidant, antimicrobial and cytotoxic potential of silver nanoparticles synthesized using flavonoid rich alcoholic leaves extract of *Reinwardtia indica*. *Drug Chem Toxicol*. 2018;42(1):1–11.
36. Rajagopal T, Jemimah IAA, Ponmanickam P, Ayyanar M. Synthesis of silver nanoparticles using *Catharanthus roseus* root extract and its larvicidal effects. *J Environ Biol*. 2015;36(6):1283.
37. Carabineiro S. Applications of gold nanoparticles in nanomedicine: recent advances in vaccines. *Molecules*. 2017;22(5):857.
38. Kaviya S, Santhanalakshmi J, Viswanathan B, Muthumary J, Srinivasan K. Biosynthesis of silver nanoparticles using *Citrus sinensis* peel extract and its antibacterial activity. *Spectrochim Acta A*. 2011;79(3):594–598.
39. Roy K. 'Green' synthesis of Silver Nanoparticles by Using Grape (*Vitis Vinifera*) Fruit Extract: Characterization of the Particles & Study of Antibacterial Activity. 2012.
40. Nayak D, Ashe S, Rauta PR, Kumari M, Nayak B. Bark extract mediated green synthesis of silver nanoparticles: evaluation of antimicrobial activity and antiproliferative response against osteosarcoma. *Mater Sci Eng C*. 2016;58:44–52.
41. Roy K, Biswas S, Banerjee PC. Synthesis of Silver nanoparticles by using grape (*Vitis vinifera*) fruit extract; characterization of the particles and study of antibacterial activity. *Research Journal of Pharmaceutical, Biological and Chemical Sciences*. 2013 ;4(1):1271–1278.
42. Singh J, Dhaliwal AS. Novel green synthesis and characterization of the antioxidant activity of silver nanoparticles prepared from *nepeta leucophylla* root extract. *Anal Lett*. 2018;52(2) :1–18.
43. Mishra MP, Padhy RN. Antibacterial activity of green silver nanoparticles synthesized from *Anogeissus acuminata* against multidrug resistant urinary tract infecting bacteria in vitro and host-toxicity testing. *J Appl Biomed*. 2018;16(2):120–125.

44. Baharara J, Namvar F, Ramezani T, Hosseini N, Mohamad R. Green synthesis of silver nanoparticles using *Achillea biebersteinii* flower extract and its anti-angiogenic properties in the rat aortic ring model. *Molecules*. 2014;19(4):4624–4634.
45. Ahmad N, Sharma S, Rai R. Rapid green synthesis of silver and gold nanoparticles using peels of *Punica granatum*. *Adv Mater Lett*. 2012;3(5):376–380.
46. Mukunthan K, Balaji S. Cashew apple juice (*Anacardium occidentale* L.) speeds up the synthesis of silver nanoparticles. *Intl J Green Nanotechnol*. 2012;4(2):71–79.
47. Kaur R, Singh J, Tripathi S. Incorporation of inorganic nanoparticles into an organic polymer matrix for data storage application. *Current Appl Phys*. 2017;17(5):756–762.
48. Raut Rajesh W, Lakkakula Jaya R, Kolekar Niranjan S, Mendhulkar Vijay D, Kashid Sahebrao B. Phytosynthesis of silver nanoparticle using *Gliricidia sepium* (Jacq.). *Curr Nanosci*. 2009;5(1):117–122.
49. Mata R, Nakkala JR, Sadras SR. Catalytic and biological activities of green silver nanoparticles synthesized from *Plumeria alba* (frangipani) flower extract. *Mater Sci Eng C*. 2015;51:216–225.
50. Benakashani F, Allafchian A, Jalali SAH. Green synthesis, characterization and antibacterial activity of silver nanoparticles from root extract of *Lepidium draba* weed. *Green Chem Lett Rev*. 2017;10(4):324–330.
51. Velayutham K, Rahuman AA, Rajakumar G, et al. Larvicidal activity of green synthesized silver nanoparticles using bark aqueous extract of *Ficus racemosa* against *Culex quinquefasciatus* and *Culex gelidus*. *Asian Pac J Trop Med*. 2013;6(2):95–101.
52. Kahrilas GA, Wally LM, Fredrick SJ, Hiskey M, Prieto AL, Owens JE. Microwave-assisted green synthesis of silver nanoparticles using orange peel extract. *ACS Sustainable Chem Eng*. 2013;2(3):367–376.
53. Gao Y, Huang Q, Su Q, Liu R. Green synthesis of silver nanoparticles at room temperature using kiwifruit juice. *Spectrosc Lett*. 2014;47(10):790–795.
54. Abdal Dayem A, Hossain MK, Lee SB, et al. The role of reactive oxygen species (ROS) in the biological activities of metallic nanoparticles. *Int J Mol Sci*. 2017;18(1):120.
55. Huang J, Li Q, Sun D, et al. Biosynthesis of silver and gold nanoparticles by novel sundried *Cinnamomum camphora* leaf. *Nanotechnology*. 2007;18(10):105104.
56. Gogoi N, Babu PJ, Mahanta C, Bora U. Green synthesis and characterization of silver nanoparticles using alcoholic flower extract of *Nyctanthes arbortristis* and in vitro investigation of their antibacterial and cytotoxic activities. *Mater Sci Eng C*. 2015;46:463–469.
57. Kumar D, Kumar G, Agrawal V. Green synthesis of silver nanoparticles using *Holarrhena antidysenterica* (L.) Wall. bark extract and their larvicidal activity against dengue and filariasis vectors. *Parasitol Res*. 2018;117(2):377–389.
58. Bankar A, Joshi B, Kumar AR, Zinjarde S. Banana peel extract mediated novel route for the synthesis of silver nanoparticles. *Colloids Surf A*. 2010;368(1):58–63.
59. Ulug B, Turkdemir MH, Cicek A, Mete A. Role of irradiation in the green synthesis of silver nanoparticles mediated by fig (*Ficus carica*) leaf extract. *Spectrochim Acta A*. 2015;135:153–161.
60. Fukui H. Development of new cosmetics based on nanoparticles. In: Naito M, Yokoyama T, Hosokawa K, Nogi K, editors. *Nanoparticle Technology Handbook*. 3rd ed. Elsevier; 2018:845–877. ISBN: 978-0-444-64110-6
61. Sasikala A, Rao ML, Savithramma N, Prasad T. Synthesis of silver nanoparticles from stem bark of *Cochlospermum religiosum* (L.) Alston: an important medicinal plant and evaluation of their antimicrobial efficacy. *Appl Nanosci*. 2015;5(7):827–835.
62. Erosa MSD, Diaz MMC, Lazcano TAR, Rodríguez MÁ, Aguilera JAR, Del Pilar González-Muñoz M. Aqueous leaf extracts of *Cnidioscolus chayamansa* (Mayan chaya) cultivated in Yucatán México. Part II: uses for the phytomediated synthesis of silver nanoparticles. *Mater Sci Eng C*. 2018;91:838–852.
63. Vijayan R, Joseph S, Mathew B. Green synthesis of silver nanoparticles using *Nervelia zeylanica* leaf extract and evaluation of their antioxidant, catalytic, and antimicrobial potentials. *Part Sci Technol*. 2018;36:1–11.
64. Fathima JB, Pugazhendhi A, Oves M, Venis R. Synthesis of eco-friendly copper nanoparticles for augmentation of catalytic degradation of organic dyes. *J Mol Liq*. 2018;260:1–8.
65. Cruz D, Falé PL, Mourato A, Vaz PD, Serralheiro ML, Lino ARL. Preparation and physicochemical characterization of Ag nanoparticles biosynthesized by *Lippia citriodora* (Lemon Verbena). *Colloids Surf B*. 2010;81(1):67–73.
66. Sharma P, Bhatt D, Zaidi M, Saradhi PP, Khanna P, Arora S. Silver nanoparticle-mediated enhancement in growth and antioxidant status of *Brassica juncea*. *Appl Biochem Biotechnol*. 2012;167(8):2225–2233.
67. Ashokkumar S, Ravi S, Velmurugan S. Green synthesis of silver nanoparticles from *Gloriosa superba* L. leaf extract and their catalytic activity. *Spectrochim Acta A Mol Biomol Spectrosc*. 2013;115:388–392.
68. Zhang J, Si G, Zou J, Fan R, Guo A, Wei X. Antimicrobial Effects of Silver Nanoparticles Synthesized by *Fatsia japonica* Leaf Extracts for Preservation of Citrus Fruits. *J Food Sci*. 2017;82(8):1861–1866.
69. McGillicuddy E, Murray I, Kavanagh S, et al. Silver nanoparticles in the environment: sources, detection and ecotoxicology. *Sci Total Environ*. 2017;575:231–246.
70. Ashokkumar S, Ravi S, Kathiravan V, Velmurugan S. Synthesis, characterization and catalytic activity of silver nanoparticles using *Tribulus terrestris* leaf extract. *Spectrochim Acta A Mol Biomol Spectrosc*. 2014;121:88–93.
71. Kumar PSM, MubarakAli D, Saratale RG, et al. Synthesis of nanocuboidal gold particles for effective antimicrobial property against clinical human pathogens. *Microb Pathog*. 2017;113:68–73.
72. Philip D, Unni C, Aromal SA, Vidhu V. Murraya koenigii leaf-assisted rapid green synthesis of silver and gold nanoparticles. *Spectrochim Acta A*. 2011;78(2):899–904.
73. Morones JR, Elechiguerra JL, Camacho A, et al. The bactericidal effect of silver nanoparticles. *Nanotechnology*. 2005;16(10):2346.
74. Vijayan SR, Santhiyagu P, Ramasamy R, et al. Seaweeds: a resource for marine bionanotechnology. *Enzyme Microb Technol*. 2016;95:45–57.
75. Veerasamy R, Xin TZ, Gunasagan S, et al. Biosynthesis of silver nanoparticles using mangosteen leaf extract and evaluation of their antimicrobial activities. *J Saudi Chem Soc*. 2011;15(2):113–120.
76. Chaudhuri RG, Paria S. Core/shell nanoparticles: classes, properties, synthesis mechanisms, characterization, and applications. *Chem Rev*. 2012;112(4):2373–2433.
77. Philip D. *Mangifera indica* leaf-assisted biosynthesis of well-dispersed silver nanoparticles. *Spectrochim Acta A*. 2011;78(1):327–331.
78. Zhu M-Q, Zhu L, Han JJ, Wu W, Hurst JK, Li AD. Spiropyran-based photochromic polymer nanoparticles with optically switchable luminescence. *J Am Chem Soc*. 2006;128(13):4303–4309.
79. Arunachalam KD, Annamalai SK, Hari S. One-step green synthesis and characterization of leaf extract-mediated biocompatible silver and gold nanoparticles from *Mimosa pudica*. *Int J Nanomedicine*. 2013;8(3):1307–1315.
80. Ulbrich K, Hola K, Subr V, Bakandritsos A, Tucek J, Zboril R. Targeted drug delivery with polymers and magnetic nanoparticles: covalent and noncovalent approaches, release control, and clinical studies. *Chem Rev*. 2016;116(9):5338–5431.

81. Singh P, Kim YJ, Yang DC. A strategic approach for rapid synthesis of gold and silver nanoparticles by Panax ginseng leaves. *Artif Cells Nanomed Biotechnol.* 2016;44(8):1949–1957.
82. Dhoble SM, Kulkarni NS. Investigation of in vitro and in vivo antifungal property of biologically synthesized copper nanoparticles (CuNP) against rhizoctonia solani a phytopathogen of soyaabean (Glycine max, L. Merrill). *Int J Eng Sci Generic Res.* 2018;4(5):17–30.
83. Wang C, Mathiyalagan R, Kim YJ, et al. Rapid green synthesis of silver and gold nanoparticles using Dendropanax moribifera leaf extract and their anticancer activities. *Int J Nanomedicine.* 2016;11:3691.
84. Payne JN, Waghwan HK, Connor MG, et al. Novel synthesis of kanamycin conjugated gold nanoparticles with potent antibacterial activity. *Front Microbiol.* 2016;7:607.
85. Hubbuck J. *Novel self patent gold nanoparticles for antineoplastic activity*: poster presented at: posters-at-capitol wisteren kenpucky university; march 3; 2016: United state of America. Available from: <https://digitalcommons.murraystate.edu/postersatthecapitol/2016/WKU/10/>
86. Kumar PV, Kala SMJ. Green Synthesis, Characterisation and Biological Activity of Platinum Nanoparticle Using Croton Caudatus Geisel Leaf Extract. *Int J Recent Res Aspects. (Special Issue:Conscientious Computing Technologies).* 2018. 608–612
87. Kouvaris P, Delimitis A, Zaspalis V, Papadopoulos D, Tsiapas SA, Michailidis N. Green synthesis and characterization of silver nanoparticles produced using Arbutus unedo leaf extract. *Mater Lett.* 2012;76:18–20.
88. Molaei R, Farhadi K, Forough M, Hajizadeh S. Green Biological Fabrication and Characterization of Highly Monodisperse Palladium Nanoparticles Using Pistacia Atlantica Fruit Broth. *J Nanostruct.* 2018;8(1):47–54.
89. Liong M, Lu J, Tamanoi F, Zink JI, Nel A. Mesoporous silica nanoparticles for biomedical applications. Google Patents; 2018.
90. Kesharwani J, Yoon KY, Hwang J, Rai M. Phytofabrication of silver nanoparticles by leaf extract of Datura metel: hypothetical mechanism involved in synthesis. *J Bionanosci.* 2009;3(1):39–44.
91. Woodard A, Xu L, Barragan AA, Nava G, Wong BM, Mangolini L. On the non-thermal plasma synthesis of nickel nanoparticles. *Plasma Processes Polym.* 2018;15(1):1700104.
92. Zayed MF, Eisa WH, Shabaka A. Malva parviflora extract assisted green synthesis of silver nanoparticles. *Spectrochim Acta A.* 2012;98:423–428.
93. Karupiah M, Rajmohan R. Green synthesis of silver nanoparticles using Ixora coccinea leaves extract. *Mater Lett.* 2013;97:141–143.
94. Raja A, Ashokkumar S, Marthandam RP, et al. Eco-friendly preparation of zinc oxide nanoparticles using Tabernaemontana divaricata and its photocatalytic and antimicrobial activity. *J Photochem Photobiol B.* 2018;181:53–58.
95. Uozumi Y, Kim K. Synthesis of Imidazo [1, 2-a] pyrimidines by A3-Coupling on CuO Nanoparticles. *Synfacts.* 2018;14(08):0883.
96. Baharara J, Ramezani T, Hosseini N, Mousavi M. Silver Nanoparticles Synthesized Coating with Zataria Multiflora Leaves Extract Induced Apoptosis in HeLa Cells Through p53 Activation. *Ijpr.* 2018;17(2):627.
97. Muthukumar H, Mohammed SN, Chandrasekaran N, Sekar AD, Pugazhendhi A, Matheswaran M. Effect of iron doped Zinc oxide nanoparticles coating in the anode on current generation in microbial electrochemical cells. *Int J Hydrogen Energy.* 2018.
98. Yakop F, Abd Ghafar SA, Yong YK, et al. Silver nanoparticles Clinacanthus Nutans leaves extract induced apoptosis towards oral squamous cell carcinoma cell lines. *Artif Cells Nanomed Biotechnol.* 2018:1–9.
99. Fard SE, Tafvizi F, Torbati MB. Silvernanoparticles biosynthesisedusingCentella asiaticaleaf extract: apoptosis induction in MCF-7 breast cancer cell line. *IET Nanobiotechnol.* 2018;12(7):994–1002. doi:10.1049/iet-nbt.2018.5069
100. Pugazhendhi A, Prabhu R, Muruganantham K, Shanmuganathan R, Natarajan S. Anticancer, antimicrobial and photocatalytic activities of green synthesized magnesium oxide nanoparticles (MgONPs) using aqueous extract of Sargassum wightii. *J Photochem Photobiol B.* 2019;190:86–97. doi:10.1016/j.jphotobiol.2018.11.014
101. Jha AK, Prasad K. Green synthesis of silver nanoparticles using Cycas leaf. *Int J Green Nanotechnol.* 2010;1(2):P110–P117. doi:10.1080/19430871003684572
102. Goutam SP, Saxena G, Singh V, Yadav AK, Bharagava RN, Thapa KB. Green synthesis of TiO2 nanoparticles using leaf extract of Jatropha curcas L. for photocatalytic degradation of tannery wastewater. *Chem Eng J.* 2018;336:386–396. doi:10.1016/j.cej.2017.12.029
103. Sisubalan N, Ramkumar VS, Pugazhendhi A, et al. ROS-mediated cytotoxic activity of ZnO and CeO 2 nanoparticles synthesized using the Rubia cordifolia L. leaf extract on MG-63 human osteosarcoma cell lines. *Environ Sci Pollut Res.* 2017;25(11):10482–10492.
104. Fathima JB, Pugazhendhi A, Venis R. Synthesis and characterization of ZrO2 nanoparticles-antimicrobial activity and their prospective role in dental care. *Microb Pathog.* 2017;110:245–251. doi:10.1016/j.micpath.2017.06.039
105. Larson JK, Carvan MJ, Hutz RJ. Engineered nanomaterials: an emerging class of novel endocrine disruptors. *Biol Reprod.* 2014;91(1):20. doi:10.1095/biolreprod.114.121434
106. Jeevanandam J, Barhoum A, Chan YS, Dufresne A, Danquah MK. Review on nanoparticles and nanostructured materials: history, sources, toxicity and regulations. *Beilstein J Nanotechnol.* 2018;9(1):1050–1074. doi:10.3762/bjnano.9.98
107. Pachapur V, Brar SK, Verma M, Surampalli RY. Nanomaterials in the Environment. In: *Nano-Ecotoxicology of Natural and Engineered Nanomaterials for Animals and Humans*. American society of civil engineering library. 2015:421–437.
108. Khan I, Saeed K, Khan I. Nanoparticles: properties, applications and toxicities. *Arabian J Chem.* 2017. doi:10.1016/j.arabjc.2017.05.011
109. Ranjit K, Baquee AA. Nanoparticle: an overview of preparation, characterization and application. *Int. Res. J. Pharm..* 2013;4(4):47–57.
110. Bhatia S. Natural Polymer Drug Delivery Systems: Nanoparticles, Plants, and Algae. Springer International Publishing. HolderSpringer International Publishing. Switzerland. 2016;1:33–93.
111. Sanjay SS, Pandey AC. A brief manifestation of nanotechnology. In: Ashutosh Kumar Shukla, editor. *EMR/ESR/EPR Spectroscopy for Characterization of Nanomaterials*. Springer; 2017:47–63.
112. Arole V, Munde S. Fabrication of Nanomaterials by Top-down and Bottom-up Approaches- An overview. *J Adv Appl Sci Technol.* 2014;1(2):89–93.
113. Thakkar KN, Mhatre SS, Parikh RY. Biological synthesis of metallic nanoparticles. *Nanomedicine.* 2010;6(2):257–262. doi:10.1016/j.nano.2009.07.002
114. Ali SW, Rajendran S, Joshi M. Synthesis and characterization of chitosan and silver loaded chitosan nanoparticles for bioactive polyester. *Carbohydr Polym.* 2011;83(2):438–446. doi:10.1016/j.carbpol.2010.08.004
115. Tejamaya M, Römer I, Merrifield RC, Lead JR. Stability of citrate, PVP, and PEG coated silver nanoparticles in ecotoxicology media. *Environ Sci Technol.* 2012;46(13):7011–7017. doi:10.1021/es2038596
116. Pal S, Tak YK, Song JM. Does the antibacterial activity of silver nanoparticles depend on the shape of the nanoparticle? A study of the gram-negative bacterium Escherichia coli. *Appl Environ Microbiol.* 2007;73(6):1712–1720. doi:10.1128/AEM.02218-06

117. Shrivastava S, Bera T, Roy A, Singh G, Ramachandrarao P, Dash D. Characterization of enhanced antibacterial effects of novel silver nanoparticles. *Nanotechnology*. 2007;18(22):225103. doi:10.1088/0957-4484/18/49/495102
118. Dubas ST, Kumlangdudsana P, Potiyaraj P. Layer-by-layer deposition of antimicrobial silver nanoparticles on textile fibers. *Colloids Surf A*. 2006;289(1):105–109. doi:10.1016/j.colsurfa.2006.04.012
119. Ahmed S, Ahmad M, Swami BL, Ikram S. A review on plants extract mediated synthesis of silver nanoparticles for antimicrobial applications: a green expertise. *J Adv Res*. 2016;7(1):17–28. doi:10.1016/j.jare.2015.02.007
120. Raveendran P, Fu J, Wallen SL. Completely “green” synthesis and stabilization of metal nanoparticles. *J Am Chem Soc*. 2003;125(46):13940–13941. doi:10.1021/ja029267j
121. Daphne J, Francis A, Mohanty R, Ojha N, Das N. Green Synthesis of Antibacterial Silver Nanoparticles using Yeast Isolates and its Characterization. *Res J Pharm Technol*. 2018;11(1):83–92. doi:10.5958/0974-360X.2018.00016.1
122. Mohamad NAN, Arham NA, Jai J, Hadi A. Plant Extract as Reducing Agent in Synthesis of Metallic Nanoparticles: A Review. *Advanced Materials Research*. 2014;832: 350–355.
123. Gomathi S, Firdous J, Bharathi V, et al. Phytochemical screening of silver nanoparticles extract of Eugenia jambolana using Fourier infrared spectroscopy. *Int J Res Pharm Sci*. 2017;8(3):383–387.
124. Banerjee P, Nath D. A phytochemical approach to synthesize silver nanoparticles for non-toxic biomedical application and study on their antibacterial efficacy. *Nanosci Technol*. 2015;2(1):1–14.
125. Hazarika D, Phukan A, Saikia E, Chetia B. Phytochemical screening and synthesis of silver nanoparticles using leaf extract of *Rhynchosyris ellipticum*. *Int J Pharm Pharm Sci*. 2014;6(1):672–674.
126. Stephen A, Seethalakshmi S. Phytochemical synthesis and preliminary characterization of silver nanoparticles using hesperidin. *J Nanosci*. 2013;2013:5. doi:10.1155/2013/126564
127. Martinez-Bernett D, Silva-Granados A, Correa-Torres S, Herrera A. Chromatographic analysis of phytochemicals components present in mangifera indica leaves for the synthesis of silver nanoparticles by AgNO₃ reduction. Paper presented at: Journal of Physics: Conference Series Vol. 687; 2016.
128. Mallikarjuna K, Sushma NJ, Narasimha G, Manoj L, Raju BDP. Phytochemical fabrication and characterization of silver nanoparticles by using Pepper leaf broth. *Arabian J Chem*. 2014;7(6):1099–1103. doi:10.1016/j.arabjc.2012.04.001
129. Kumar B, Smita K, Cumbal L, Debut A. Green synthesis of silver nanoparticles using Andean blackberry fruit extract. *Saudi J Biol Sci*. 2017;24(1):45–50. doi:10.1016/j.sjbs.2015.09.006
130. Kumar CMK, Yugandhar P, Savithramma N. Biological synthesis of silver nanoparticles from *Adansonia digitata* L. fruit pulp extract, characterization, and its antimicrobial properties. *J Intercult Ethnopharmacol*. 2016;5(1):79. doi:10.5455/jice.
131. Malaikozhundan B, Vijayakumar S, Vaseeharan B, et al. Two potential uses for silver nanoparticles coated with *Solanum nigrum* unripe fruit extract: biofilm inhibition and photodegradation of dye effluent. *Microb Pathog*. 2017;111:316–324. doi:10.1016/j.micpath.2017.08.039
132. Rad MS, Rad JS, Heshmati GA, Miri A, Sen DJ. Biological synthesis of gold and silver nanoparticles by *Nitraria schoberi* fruits. *Open J Adv Drug Delivery*. 2013;1(2):174–179.
133. Naganathan K, Thirunavukkarasu S. Green way genesis of silver nanoparticles using multiple fruit peels waste and its antimicrobial, anti-oxidant and anti-tumor cell line studies. Paper presented at 2nd International Conference on Mining, Material and Metallurgical Engineering: IOP Conference Series: Materials Science and Engineering191; 2017. doi:10.1088/1757-899X/191/1/012009
134. Song JY, Kim BS. Rapid biological synthesis of silver nanoparticles using plant leaf extracts. *Bioprocess Biosyst Eng*. 2009;32(1):79. doi:10.1007/s00449-008-0224-6
135. Huang H, Yang X. Synthesis of polysaccharide-stabilized gold and silver nanoparticles: a green method. *Carbohydr Res*. 2004;339(15):2627–2631. doi:10.1016/j.carres.2004.08.005
136. Vigneshwaran N, Nachane R, Balasubramanya R, Varadarajan P. A novel one-pot ‘green’ synthesis of stable silver nanoparticles using soluble starch. *Carbohydr Res*. 2006;341(12):2012–2018. doi:10.1016/j.carres.2006.04.042
137. Guidelli EJ, Ramos AP, Zaniquelli MED, Baffa O. Green synthesis of colloidal silver nanoparticles using natural rubber latex extracted from *Hevea brasiliensis*. *Spectrochim Acta A*. 2011;82(1):140–145. doi:10.1016/j.saa.2011.07.024
138. Shamel K, Ahmad MB, Zamanian A, et al. Green biosynthesis of silver nanoparticles using *Curcuma longa* tuber powder. *Int J Nanomedicine*. 2012;7:5603. doi:10.2147/IJN.S30631
139. Umoren S, Obot I, Gasem Z. Green synthesis and characterization of silver nanoparticles using red apple (*Malus domestica*) fruit extract at room temperature. *J Mater Environ Sci*. 2014;5:907–914.
140. Lu R, Yang D, Cui D, Wang Z, Guo L. Egg white-mediated green synthesis of silver nanoparticles with excellent biocompatibility and enhanced radiation effects on cancer cells. *Int J Nanomed*. 2012;7:2101. doi:10.2147/IJN.S30631
141. Masurkar SA, Chaudhari PR, Shidore VB, Kamble SP. Rapid biosynthesis of silver nanoparticles using *Cymbopogon citratus* (lemongrass) and its antimicrobial activity. *Nano-Micro Lett*. 2011;3(3):189–194. doi:10.1007/BF03353671
142. Nadagouda MN, Varma RS. Green synthesis of silver and palladium nanoparticles at room temperature using coffee and tea extract. *Green Chem*. 2008;10(8):859–862. doi:10.1039/b804703k
143. Begum NA, Mondal S, Basu S, Laskar RA, Mandal D. Biogenic synthesis of Au and Ag nanoparticles using aqueous solutions of Black Tea leaf extracts. *Colloids Surf B*. 2009;71(1):113–118. doi:10.1016/j.colsurfb.2009.01.012
144. Pande N, Jaspal DK, Ambekar J. Ecofriendly synthesis and applications of silver nanoparticles. *J Chem Pharm Res*. 2014;6(9):403–410.
145. Awwad AM, Salem NM, Abdeen AO. Green synthesis of silver nanoparticles using carob leaf extract and its antibacterial activity. *Int J Ind Chem*. 2013;4(1):29. doi:10.1186/2228-5547-4-29
146. Sulaiman GM, Mohammed WH, Marzoug TR, Al-Amiery AAA, Kadhum AAH, Mohamad AB. Green synthesis, antimicrobial and cytotoxic effects of silver nanoparticles using *Eucalyptus chapmaniana* leaves extract. *Asian Pac J Trop Biomed*. 2013;3(1):58–63. doi:10.1016/S2221-1691(13)60024-6
147. Mousavi B, Tafvizi F, Zaker Bostanabad S. Green synthesis of silver nanoparticles using *Artemisia turcomanica* leaf extract and the study of anti-cancer effect and apoptosis induction on gastric cancer cell line (AGS). *Artif Cells Nanomed Biotechnol*. 2018;46(11):1–12. doi:10.1080/21691401.2018.1430697
148. Kumara V, Vermab S, Choudhury S, Tyagid M, Chatterjee S, Variyara PS. Biocompatible silver nanoparticles from vegetable waste: its characterization and bio-efficacy. *Int J Nano Matl Sci*. 2015;4(1):70–86.
149. Sathishkumar M, Sneha K, Won S, Cho C-W, Kim S, Yun Y-S. Cinnamon zeylanicum bark extract and powder mediated green synthesis of nano-crystalline silver particles and its bactericidal activity. *Colloids Surf B*. 2009;73(2):332–338. doi:10.1016/j.colsurfb.2009.06.005
150. Ojha S. *Green Synthesis of Metallic Nanoparticles Using Leaf Extract of Selected Silkworm Host Plants and Their Applications*. Indian institute of technology Guwahati. Department of Biosciences and Bioengineering; 2018.

151. Jebakumar Immanuel Edison TN, Sethuraman MG. Electrocatalytic reduction of benzyl chloride by green synthesized silver nanoparticles using pod extract of *Acacia nilotica*. *ACS Sustainable Chem Eng*. 2013;1(10):1326–1332. doi:10.1021/sc4001725
152. Mallikarjuna K, Narasimha G, Dillip G, et al. Green synthesis of silver nanoparticles using Ocimum leaf extract and their characterization. *Dig J Nanomater Biostruct*. 2011;6(1):181–186.
153. Satyavani K, Ramanathan T, Gurudeeban S. Plant mediated synthesis of biomedical silver nanoparticles by using leaf extract of *Citrullus colocynthis*. *Res J Nanosci Nanotechnol*. 2011;1(2):95–101. doi:10.3923/rjnn.2011.95.101
154. Arunachalam R, Dhanasingh S, Kalimuthu B, Uthirappan M, Rose C, Mandal AB. Phytosynthesis of silver nanoparticles using *Coccinia grandis* leaf extract and its application in the photocatalytic degradation. *Colloids Surf B*. 2012;94:226–230. doi:10.1016/j.colsurfb.2012.01.040
155. Gopinath K, Gowri S, Arumugam A. Phytosynthesis of silver nanoparticles using *Pterocarpus santalinus* leaf extract and their antibacterial properties. *J Nanostruct Chem*. 2013;3(1):68. doi:10.1186/2193-8865-3-68
156. Vanaja M, Annadurai G. *Coleus aromaticus* leaf extract mediated synthesis of silver nanoparticles and its bactericidal activity. *Appl Nanosci*. 2013;3(3):217–223. doi:10.1007/s13204-012-0121-9
157. Bar H, Bhui DK, Sahoo GP, Sarkar P, Pyne S, Misra A. Green synthesis of silver nanoparticles using seed extract of *Jatropha curcas*. *Colloids Surf A*. 2009;348(1):212–216. doi:10.1016/j.colsurfa.2009.07.021
158. Kathiravan V, Ravi S, Ashokkumar S. Synthesis of silver nanoparticles from *Melia dubia* leaf extract and their in vitro anticancer activity. *Spectrochim Acta A*. 2014;130:116–121. doi:10.1016/j.saa.2014.03.107
159. Li S, Shen Y, Xie A, et al. Green synthesis of silver nanoparticles using *Capsicum annuum* L. extract. *Green Chem*. 2007;9(8):852–858. doi:10.1039/b615357g
160. Vivek R, Thangam R, Muthuchelian K, Gunasekaran P, Kaveri K, Kannan S. Green biosynthesis of silver nanoparticles from *Annona squamosa* leaf extract and its in vitro cytotoxic effect on MCF-7 cells. *Process Biochem*. 2012;47(12):2405–2410. doi:10.1016/j.procbio.2012.09.025
161. Loo YY, Chieng BW, Nishibuchi M, Radu S. Synthesis of silver nanoparticles by using tea leaf extract from *Camellia sinensis*. *Int J Nanomedicine*. 2012;7:4263. doi:10.2147/IJN.S30631
162. Ajitha B, Reddy YAK, Reddy PS. Green synthesis and characterization of silver nanoparticles using *Lantana camara* leaf extract. *Mater Sci Eng C*. 2015;49:373–381. doi:10.1016/j.msec.2015.01.035
163. Sathyavathi R, Krishna MB, Rao SV, Saritha R, Rao DN. Biosynthesis of silver nanoparticles using *Coriandrum sativum* leaf extract and their application in nonlinear optics. *Adv Sci Lett*. 2010;3(2):138–143. doi:10.1166/asl.2010.1099
164. Chandran SP, Chaudhary M, Pasricha R, Ahmad A, Sastry M. Synthesis of gold nanotriangles and silver nanoparticles using *Aloe vera* plant extract. *Biotechnol Prog*. 2006;22(2):577–583. doi:10.1021/bp0501423
165. Elavazhagan T, Arunachalam KD. Memecylon edule leaf extract mediated green synthesis of silver and gold nanoparticles. *Int J Nanomed*. 2011;6:1265–1278. doi:10.2147/IJN.S18347
166. Philip D. Green synthesis of gold and silver nanoparticles using *Hibiscus rosa sinensis*. *Phys E*. 2010;42(5):1417–1424. doi:10.1016/j.physe.2009.11.081
167. Reddy NJ, Vali DN, Rani M, Rani SS. Evaluation of antioxidant, antibacterial and cytotoxic effects of green synthesized silver nanoparticles by *Piper longum* fruit. *Mater Sci Eng C*. 2014;34:115–122. doi:10.1016/j.msec.2013.08.039
168. Mallikarjuna K, Balasubramanyam K, Narasimha G, Kim H. Phyto-synthesis and antibacterial studies of bio-based silver nanoparticles using *Sesbania grandiflora* (Avisa) leaf tea extract. *Mater Res Express*. 2018;5(1):015054. doi:10.1088/2053-1591/aaa67d
169. Vasanth K, Ilango K, MohanKumar R, Agrawal A, Dubey GP. Anticancer activity of *Moringa oleifera* mediated silver nanoparticles on human cervical carcinoma cells by apoptosis induction. *Colloids Surf B*. 2014;117:354–359. doi:10.1016/j.colsurfb.2014.02.052
170. Sankar R, Karthik A, Prabu A, Karthik S, Shivashangari KS, Ravikumar V. *Origanum vulgare* mediated biosynthesis of silver nanoparticles for its antibacterial and anticancer activity. *Colloids Surf B*. 2013;108:80–84. doi:10.1016/j.colsurfb.2013.02.033
171. Prabhu D, Arulvasu C, Babu G, Manikandan R, Srinivasan P. Biologically synthesized green silver nanoparticles from leaf extract of *Vitex negundo* L. induce growth-inhibitory effect on human colon cancer cell line HCT15. *Process Biochem*. 2013;48(2):317–324. doi:10.1016/j.procbio.2012.12.013
172. Rajaram K, Aiswarya D, Sureshkumar P. Green synthesis of silver nanoparticle using *Tephrosia tinctoria* and its antidiabetic activity. *Mater Lett*. 2015;138:251–254. doi:10.1016/j.matlet.2014.10.017
173. Kumar HAK, Mandal BK, Kumar KM, et al. Antimicrobial and antioxidant activities of *Mimusops elengi* seed extract mediated isotropic silver nanoparticles. *Spectrochim Acta A*. 2014;130:13–18. doi:10.1016/j.saa.2014.03.024
174. Kumar DA, Palanichamy V, Roopan SM. Green synthesis of silver nanoparticles using *Alternanthera dentata* leaf extract at room temperature and their antimicrobial activity. *Spectrochim Acta A*. 2014;127:168–171. doi:10.1016/j.saa.2014.02.058
175. Nabikhan A, Kandasamy K, Raj A, Alikunhi NM. Synthesis of antimicrobial silver nanoparticles by callus and leaf extracts from saltmarsh plant, *Sesuvium portulacastrum* L. *Colloids Surf B*. 2010;79(2):488–493. doi:10.1016/j.colsurfb.2010.05.018
176. Muniyappan N, Nagarajan N. Green synthesis of silver nanoparticles with *Dalbergia spinosa* leaves and their applications in biological and catalytic activities. *Process Biochem*. 2014;49(6):1054–1061. doi:10.1016/j.procbio.2014.03.015
177. David L, Moldovan B, Vulcu A, et al. Green synthesis, characterization and anti-inflammatory activity of silver nanoparticles using European black elderberry fruits extract. *Colloids Surf B*. 2014;122:767–777. doi:10.1016/j.colsurfb.2014.08.018
178. Savitha R, Saraswathi U. A study on the preventive effect of silver nano particles synthesized from *millingtonia hortensis* in isoproterenol induced cardio toxicity in male wistar rats. *World J Pharm Pharm Sci*. 2016;5(8):1442–1450.
179. Atale N, Saxena S, Nirmala JG, Narendhirakannan R, Mohanty S, Rani V. Synthesis and characterization of *Syzygium cumini* nanoparticles for its protective potential in high glucose-induced cardiac stress: a green approach. *Appl Biochem Biotechnol*. 2017;181(3):1140–1154. doi:10.1007/s12010-016-2274-6
180. Chitra G, Balasubramani G, Ramkumar R, Sowmiya R, Perumal P. *Mukia maderaspatana* (Cucurbitaceae) extract-mediated synthesis of silver nanoparticles to control *Culex quinquefasciatus* and *Aedes aegypti* (Diptera: Culicidae). *Parasitol Res*. 2015;114(4):1407–1415. doi:10.1007/s00436-015-4320-7
181. Santhoshkumar T, Rahuman AA, Rajakumar G, et al. Synthesis of silver nanoparticles using *Nelumbo nucifera* leaf extract and its larvicidal activity against malaria and filariasis vectors. *Parasitol Res*. 2011;108(3):693–702. doi:10.1007/s00436-010-2115-4
182. Gnanadesigan M, Anand M, Ravikumar S, et al. Biosynthesis of silver nanoparticles by using mangrove plant extract and their potential mosquito larvicidal property. *Asian Pac J Trop Med*. 2011;4(10):799–803. doi:10.1016/S1995-7645(11)60197-1

183. Li X, Xu H, Chen Z-S, Chen G. Biosynthesis of nanoparticles by microorganisms and their applications. *J Nanomater.* **2011**;2011:16. doi:10.1155/2011/270974
184. Otari S, Patil R, Ghosh S, Thorat N, Pawar S. Intracellular synthesis of silver nanoparticle by actinobacteria and its antimicrobial activity. *Spectrochim Acta A.* **2015**;136:1175–1180. doi:10.1016/j.saa.2014.10.003
185. Kannan N, Subbalaxmi S. Green synthesis of silver nanoparticles using *Bacillus subtilis* IA751 and its antimicrobial activity. *Res J Nanosci Nanotechnol.* **2011**;1(2):87–94. doi:10.3923/rjnn.2011.87.94
186. Malarkodi C, Rajeshkumar S, Paulkumar K, Gnanajobitha G, Vanaja M, Annadurai G. Bacterial synthesis of silver nanoparticles by using optimized biomass growth of *Bacillus* sp. *J Nanosci Nanotechnol.* **2013**;3:26–32.
187. Hallol M. *Studies on Bacterial Synthesis of Silver Nanoparticles Using Gamma Radiation and Their Activity against Some Pathogenic Microbes.* Cairo (Egypt): Department of Microbiology and Immunology, Cairo University; **2013**.
188. Das VL, Thomas R, Varghese RT, Soniya E, Mathew J, Radhakrishnan E. Extracellular synthesis of silver nanoparticles by the *Bacillus* strain CS 11 isolated from industrialized area. *Biotech.* **2014**;4(2):121–126. doi:10.1007/s13205-013-0130-8
189. Saravanan C, Rajesh R, Kaviarasan T, Muthukumar K, Kavitha D, Shetty PH. Synthesis of silver nanoparticles using bacterial exopolysaccharide and its application for degradation of azo-dyes. *Biotechnol Rep.* **2017**;15:33–40. doi:10.1016/j.btre.2017.02.006
190. Gandhi H, Khan S. Biological synthesis of silver nanoparticles and its antibacterial activity. *J Nanomed Nanotechnol.* **2016**;7(2):366. doi:10.4172/2157-7439.1000366
191. Sadhasivam S, Shanmugam P, Yun K. Biosynthesis of silver nanoparticles by *Streptomyces hygroscopicus* and antimicrobial activity against medically important pathogenic microorganisms. *Colloids Surf B.* **2010**;81(1):358–362. doi:10.1016/j.colsurfb.2010.07.036
192. Sintubin L, De Windt W, Dick J, et al. Lactic acid bacteria as reducing and capping agent for the fast and efficient production of silver nanoparticles. *Appl Microbiol Biotechnol.* **2009**;84(4):741–749. doi:10.1007/s00253-009-2032-6
193. Shahverdi AR, Minaeian S, Shahverdi HR, Jamalifar H, Nohi A-A. Rapid synthesis of silver nanoparticles using culture supernatants of Enterobacteria: a novel biological approach. *Process Biochem.* **2007**;42(5):919–923. doi:10.1016/j.procbio.2007.02.005
194. Parikh RY, Ramanathan R, Coloe PJ, et al. Genus-wide physicochemical evidence of extracellular crystalline silver nanoparticles biosynthesis by *Morganella* spp. *PLoS One.* **2011**;6(6):e21401. doi:10.1371/journal.pone.0021401
195. Gurunathan S, Kalishwaralal K, Vaidyanathan R, et al. Biosynthesis, purification and characterization of silver nanoparticles using *Escherichia coli*. *Colloids Surf B.* **2009**;74(1):328–335. doi:10.1016/j.colsurfb.2009.07.048
196. Shivaji S, Madhu S, Singh S. Extracellular synthesis of antibacterial silver nanoparticles using psychrophilic bacteria. *Process Biochem.* **2011**;46(9):1800–1807. doi:10.1016/j.procbio.2011.06.008
197. Nanda A, Saravanan M. Biosynthesis of silver nanoparticles from *Staphylococcus aureus* and its antimicrobial activity against MRSA and MRSE. *Nanomedicine.* **2009**;5(4):452–456. doi:10.1016/j.nano.2009.01.012
198. Saravanan M, Barik SK, MubarakAli D, Prakash P, Pugazhendhi A. Synthesis of silver nanoparticles from *Bacillus brevis* (NCIM 2533) and their antibacterial activity against pathogenic bacteria. *Microb Pathog.* **2018**;116:221–226. doi:10.1016/j.micpath.2018.01.038
199. Merin DD, Prakash S, Bhimba BV. Antibacterial screening of silver nanoparticles synthesized by marine micro algae. *Asian Pac J Trop Med.* **2010**;3(10):797–799. doi:10.1016/S1995-7645(10)60191-5
200. Prasad TN, Kambala VSR, Naidu R. Phyconanotechnology: synthesis of silver nanoparticles using brown marine algae *Cystophora moniliformis* and their characterisation. *J Appl Phycol.* **2013**;25(1):177–182. doi:10.1007/s10811-012-9851-z
201. Govindaraju K, Kiruthiga V, Kumar VG, Singaravelu G. Extracellular synthesis of silver nanoparticles by a marine alga, *Sargassum wightii* Grevilli and their antibacterial effects. *J Nanosci Nanotechnol.* **2009**;9(9):5497–5501.
202. Kathiraven T, Sundaramanickam A, Shanmugam N, Balasubramanian T. Green synthesis of silver nanoparticles using marine algae *Caulerpa racemosa* and their antibacterial activity against some human pathogens. *Appl Nanosci.* **2015**;5(4):499–504. doi:10.1007/s13204-014-0341-2
203. El-Rafie H, El-Rafie M, Zahran M. Green synthesis of silver nanoparticles using polysaccharides extracted from marine macro algae. *Carbohydr Polym.* **2013**;96(2):403–410. doi:10.1016/j.carbpol.2013.03.071
204. Kannan RRR, Arumugam R, Ramya D, Manivannan K, Anantharaman P. Green synthesis of silver nanoparticles using marine macroalga *Chaetomorpha linum*. *Appl Nanosci.* **2013**;3(3):229–233. doi:10.1007/s13204-012-0125-5
205. Pugazhendhi A, Prabakar D, Jacob JM, Karuppusamy I, Saratale RG. Synthesis and characterization of silver nanoparticles using *Gelidium amansii* and its antimicrobial property against various pathogenic bacteria. *Microb Pathog.* **2018**;114:41–45. doi:10.1016/j.micpath.2017.11.013
206. Ahmad A, Mukherjee P, Senapati S, et al. Extracellular biosynthesis of silver nanoparticles using the fungus *Fusarium oxysporum*. *Colloids Surf B.* **2003**;28(4):313–318. doi:10.1016/S0927-7765(02)00174-1
207. Mukherjee P, Ahmad A, Mandal D, et al. Fungus-mediated synthesis of silver nanoparticles and their immobilization in the mycelial matrix: a novel biological approach to nanoparticle synthesis. *Nano Lett.* **2001**;1(10):515–519. doi:10.1021/nl0155274
208. Bhainsa KC, D'Souza S. Extracellular biosynthesis of silver nanoparticles using the fungus *Aspergillus fumigatus*. *Colloids Surf B.* **2006**;47(2):160–164. doi:10.1016/j.colsurfb.2005.11.026
209. Kathiresan K, Manivannan S, Nabeel M, Dhivya B. Studies on silver nanoparticles synthesized by a marine fungus, *Penicillium fellutanum* isolated from coastal mangrove sediment. *Colloids Surf B.* **2009**;71(1):133–137. doi:10.1016/j.colsurfb.2009.01.016
210. Vigneshwaran N, Ashtaputre N, Varadarajan P, Nachane R, Paralakar K, Balasubramanya R. Biological synthesis of silver nanoparticles using the fungus *Aspergillus flavus*. *Mater Lett.* **2007**;61(6):1413–1418. doi:10.1016/j.matlet.2006.07.042
211. Basavaraja S, Balaji S, Lagashetty A, Rajasab A, Venkataraman A. Extracellular biosynthesis of silver nanoparticles using the fungus *Fusarium semitectum*. *Mater Res Bull.* **2008**;43(5):1164–1170. doi:10.1016/j.materresbull.2007.06.020
212. Gajbhiye M, Kesharwani J, Ingle A, Gade A, Rai M. Fungus-mediated synthesis of silver nanoparticles and their activity against pathogenic fungi in combination with fluconazole. *Nanomedicine.* **2009**;5(4):382–386. doi:10.1016/j.nano.2009.06.005
213. Banu A, Rathod V, Ranganath E. Silver nanoparticle production by *Rhizopus stolonifer* and its antibacterial activity against extended spectrum β -lactamase producing (ESBL) strains of enterobacteriaceae. *Mater Res Bull.* **2011**;46(9):1417–1423. doi:10.1016/j.materresbull.2011.05.008

214. Saravanan M, Arokiyaraj S, Lakshmi T, Pugazhendhi A. Synthesis of silver nanoparticles from *Phenerochaete chrysosporium* (MTCC-787) and their antibacterial activity against human pathogenic bacteria. *Microb Pathog.* **2018**;117:68–72. doi:10.1016/j.micpath.2018.02.008
215. Wei G, Zhou H, Liu Z, et al. One-step synthesis of silver nanoparticles, nanorods, and nanowires on the surface of DNA network. *J Phys Chem B.* **2005**;109(18):8738–8743. doi:10.1021/jp044314a
216. Nithyaja B, Misha H, Nampoori V. Synthesis of silver nanoparticles in DNA template and its influence on nonlinear optical properties. *Nanosci Nanotechnol.* **2012**;2(4):99–103. doi:10.5923/j.nn.20120204.02
217. Kasyanenko N, Varshavskii M, Ikonnikov E, et al. DNA modified with metal nanoparticles: preparation and characterization of ordered metal-DNA nanostructures in a solution and on a substrate. *J Nanomater.* **2016**;2016:12. doi:10.1155/2016/3237250
218. Dai S, Zhang X, Li T, Du Z, Dang H. Preparation of silver nanopatterns on DNA templates. *Appl Surf Sci.* **2005**;249(1–4):346–353. doi:10.1016/j.apsusc.2004.12.026
219. Naik RR, Stringer SJ, Agarwal G, Jones SE, Stone MO. Biomimetic synthesis and patterning of silver nanoparticles. *Nat Mater.* **2002**;1(3):169. doi:10.1038/nmat758
220. Patil MP, Singh RD, Koli PB, et al. Antibacterial potential of silver nanoparticles synthesized using *Madhuca longifolia* flower extract as a green resource. *Microb Pathog.* **2018**;121:184–189. doi:10.1016/j.micpath.2018.05.040
221. Verma VC, Kharwar RN, Gange AC. Biosynthesis of antimicrobial silver nanoparticles by the endophytic fungus *Aspergillus clavatus*. *Nanomedicine.* **2010**;5(1):33–40. doi:10.2217/nmm.09.77
222. Abdel-Aziz MS, Shaheen MS, El-Nekeety AA, Abdel-Wahhab MA. Antioxidant and antibacterial activity of silver nanoparticles biosynthesized using *Chenopodium murale* leaf extract. *J Saudi Chem Soc.* **2014**;18(4):356–363. doi:10.1016/j.jscs.2013.09.011
223. Dipankar C, Murugan S. The green synthesis, characterization and evaluation of the biological activities of silver nanoparticles synthesized from *Iresine herbstii* leaf aqueous extracts. *Colloids Surf B.* **2012**;98:112–119. doi:10.1016/j.colsurfb.2012.04.006
224. Bindhu M, Umadevi M. Antibacterial and catalytic activities of green synthesized silver nanoparticles. *Spectrochim Acta A.* **2015**;135:373–378. doi:10.1016/j.saa.2014.07.045
225. Ghosh S, Patil S, Ahire M, et al. Synthesis of silver nanoparticles using *Dioscorea bulbifera* tuber extract and evaluation of its synergistic potential in combination with antimicrobial agents. *Int J Nanomed.* **2012**;7:483. doi:10.2147/IJN.S30631
226. Manikandan R, Manikandan B, Raman T, et al. Biosynthesis of silver nanoparticles using ethanolic petals extract of *Rosa indica* and characterization of its antibacterial, anticancer and anti-inflammatory activities. *Spectrochim Acta A.* **2015**;138:120–129. doi:10.1016/j.saa.2014.10.043
227. Patil RS, Kokate MR, Kolekar SS. Bioinspired synthesis of highly stabilized silver nanoparticles using *Ocimum tenuiflorum* leaf extract and their antibacterial activity. *Spectrochim Acta A.* **2012**;91:234–238. doi:10.1016/j.saa.2012.02.009
228. Wongpreecha J, Polpanich D, Suteewong T, Kaewsaneha C, Tangboriboonrat P. One-pot, large-scale green synthesis of silver nanoparticles-chitosan with enhanced antibacterial activity and low cytotoxicity. *Carbohydr Polym.* **2018**;199:641–648. doi:10.1016/j.carbpol.2018.07.039
229. Lok C-N, Ho C-M, Chen R, et al. Silver nanoparticles: partial oxidation and antibacterial activities. *JBIC.* **2007**;12(4):527–534. doi:10.1007/s00775-007-0208-z
230. Martinez-Castanon G, Nino-Martinez N, Martinez-Gutierrez F, Martinez-Mendoza J, Ruiz F. Synthesis and antibacterial activity of silver nanoparticles with different sizes. *J Nanopart Res.* **2008**;10(8):1343–1348. doi:10.1007/s11051-008-9428-6
231. Asghar MA, Zahir E, Shahid SM, et al. Iron, copper and silver nanoparticles: green synthesis using green and black tea leaves extracts and evaluation of antibacterial, antifungal and aflatoxin B 1 adsorption activity. *LWT.* **2018**;90:98–107. doi:10.1016/j.lwt.2017.12.009
232. Khatami M, Sharifi I, Nobre MA, Zafarnia N, Aflatoonian MR. Waste-grass-mediated green synthesis of silver nanoparticles and evaluation of their anticancer, antifungal and antibacterial activity. *Green Chem Lett Rev.* **2018**;11(2):125–134. doi:10.1080/17518253.2018.1444797
233. Muthamil S, Devi VA, Balasubramaniam B, Balamurugan K, Pandian SK. Green synthesized silver nanoparticles demonstrating enhanced in vitro and in vivo antibiofilm activity against *Candida* spp. *J Basic Microbiol.* **2018**;58(4):343–357. doi:10.1002/jobm.201700529
234. Bonilla JJA, Guerrero DJP, Rgt S, et al. Green synthesis of silver nanoparticles using maltose and cysteine and their effect on cell wall envelope shapes and microbial growth of *Candida* spp. *J Nanosci Nanotechnol.* **2017**;17(3):1729–1739. doi:10.1166/jnn.2017.12822
235. Marulasiddeshwara M, Dakshayani S, Kumar MS, Chethana R, Kumar PR, Devaraja S. Facile-one pot-green synthesis, antibacterial, antifungal, antioxidant and antiplatelet activities of lignin capped silver nanoparticles: a promising therapeutic agent. *Mater Sci Eng C.* **2017**;81:182–190. doi:10.1016/j.msec.2017.07.054
236. Sonker AS, Pathak J, Kannaujiya V, Sinha R, Pathak J, Kannaujiya V. Characterization and in vitro antitumor, antibacterial and antifungal activities of green synthesized silver nanoparticles using cell extract of *Nostoc* sp. strain HKAR-2. *Can J Biotechnol.* **2017**;1(1):26–37. doi:10.24870/cjb.2017-000103
237. Phull A-R, Abbas Q, Ali A, Raza H, Zia M, Haq I-U. Antioxidant, cytotoxic and antimicrobial activities of green synthesized silver nanoparticles from crude extract of *Bergenia ciliata*. *Future J Pharm Sci.* **2016**;2(1):31–36. doi:10.1016/j.fjps.2016.03.001
238. Khatami M, Nejad MS, Salari S, Almani PGN. Plant-mediated green synthesis of silver nanoparticles using *Trifolium resupinatum* seed exudate and their antifungal efficacy on *Neofusicoccum parvum* and *Rhizoctonia solani*. *IET Nanobiotechnol.* **2016**;10(4):237–243. doi:10.1049/iet-nbt.2015.0078
239. Sánchez-Navarro M, Ruiz-Torres CA, Niño-Martínez N, et al. Cytotoxic and bactericidal effect of silver nanoparticles obtained by green synthesis method using *annona muricata* aqueous extract and functionalized with 5-fluorouracil. *Bioinorg Chem Appl.* **2018**;2018:8. doi:10.1155/2018/6506381
240. Lakshmanan G, Sathiyaseelan A, Kalaihelvan P, Murugesan K. Plant-mediated synthesis of silver nanoparticles using fruit extract of *Cleome viscosa* L.: assessment of their antibacterial and anticancer activity. *Karbala Int J Mod Sci.* **2018**;4(1):61–68.
241. Elella MHA, Mohamed RR, Abdel-Aziz MM, Sabaa MW. Green synthesis of antimicrobial and antitumor N, N, N-trimethyl chitosan chloride/poly (acrylic acid)/silver nanocomposites. *Int J Biol Macromol.* **2018**;111:706–716.
242. Palem RR, Ganesh SD, Kroneková Z, Sláviková M, Saha N, Saha P. Green synthesis of silver nanoparticles and biopolymer nanocomposites: a comparative study on physico-chemical, antimicrobial and anticancer activity. *Bull Mate Sci.* **2018**;41(2):55.
243. Dadashpour M, Firouzi-Amandi A, Pourhassan-Moghaddam M, et al. Biomimetic synthesis of silver nanoparticles using *Matricaria chamomilla* extract and their potential anticancer activity against human lung cancer cells. *Mater Sci Eng C.* **2018**;92:902–912.
244. Oves M, Aslam M, Rauf MA, et al. Antimicrobial and anticancer activities of silver nanoparticles synthesized from the root hair extract of *Phoenix dactylifera*. *Mater Sci Eng.* **2018**;89:429–443.

245. Sun RW-Y, Chen R, Chung NP-Y, Ho C-M, Lin C-LS, Che C-M. Silver nanoparticles fabricated in Hepes buffer exhibit cytoprotective activities toward HIV-1 infected cells. *Cheml Commun.* **2005**;40:5059–5061.
246. Zodrow K, Brunet L, Mahendra S, et al. Polysulfone ultrafiltration membranes impregnated with silver nanoparticles show improved biofouling resistance and virus removal. *Water Res.* **2009**;43(3):715–723.
247. Hebeish A, El-Rafie M, El-Sheikh M, Seleem AA, El-Naggar ME. Antimicrobial wound dressing and anti-inflammatory efficacy of silver nanoparticles. *Int J Biol Macromol.* **2014**;65:509–515.
248. Maneerung T, Tokura S, Rujiravanit R. Impregnation of silver nanoparticles into bacterial cellulose for antimicrobial wound dressing. *Carbohydr Polym.* **2008**;72(1):43–51.
249. Chen J-P, Chiang Y. Bioactive electrospun silver nanoparticles-containing polyurethane nanofibers as wound dressings. *J Nanosci Nanotechnol.* **2010**;10(11):7560–7564.
250. Jacob JM, John MS, Jacob A, et al. Bactericidal coating of paper towels via sustainable biosynthesis of silver nanoparticles using *Ocimum sanctum* leaf extract. *Mater Res Express.* **2018**;6(4):45401.

International Journal of Nanomedicine

Dovepress

Publish your work in this journal

The International Journal of Nanomedicine is an international, peer-reviewed journal focusing on the application of nanotechnology in diagnostics, therapeutics, and drug delivery systems throughout the biomedical field. This journal is indexed on PubMed Central, MedLine, CAS, SciSearch®, Current Contents®/Clinical Medicine,

Journal Citation Reports/Science Edition, EMBase, Scopus and the Elsevier Bibliographic databases. The manuscript management system is completely online and includes a very quick and fair peer-review system, which is all easy to use. Visit <http://www.dovepress.com/testimonials.php> to read real quotes from published authors.

Submit your manuscript here: <https://www.dovepress.com/international-journal-of-nanomedicine-journal>